CHEMICAL SEASONING

By W. KARL LOUGHBOROUGH*

# of Douglas Fir

Research Studies by Forest Products Laboratory Point to the Value Of Chemically Seasoning Wood to Prevent Checking and Shrinking

AS A result of the preliminary article on the Forest Products Laboratory method of seasoning wood with chemicals, which appeared in BARREL AND BOX AND PACKAGES, September, 1936, considerable interest has been manifested in the subject by the lumber industry. The available information evidently needs to be focused so that, the industry can judge the commercial possibilities of the process.

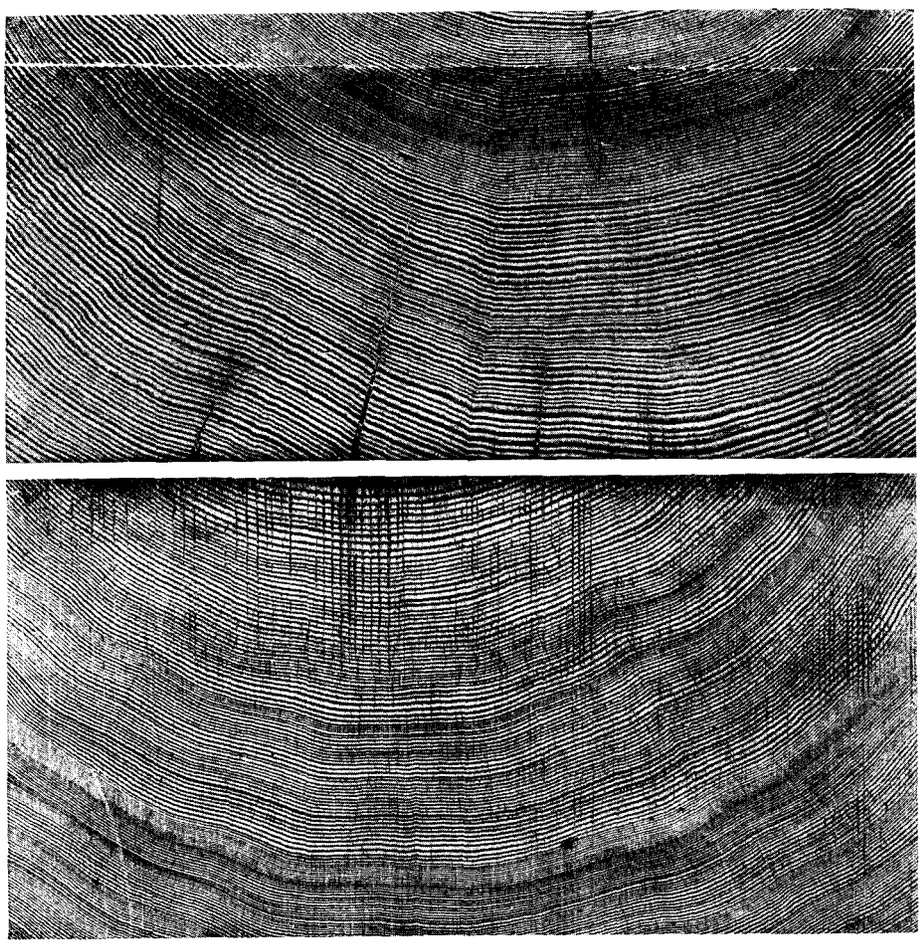

Sections of 6 in. by 12 in. Douglas fir timbers. Above—Afterair seasoning to a moisture content of 15 per cent. Below—Afterchemical seasoning to a moisture content of six per cent

When normal wood is subjected long enough to a given constant temperature and relative humidity, it will attain a moisture content that is in equilibrium with the surrounding atmosphere. This moisture condition is known as the equilibrium moisture content and with minor exceptions is the same for all native species of wood. When wood attains an equilibrium moisture content, its contained moisture has the same vapor pressure as the surrounding atmosphere. If, however, the hygroscopic moisture acts as a solvent for a chemical its vapor pressure will be reduced varying degrees depending upon the characteristics of the dissolved chemical. Consequently, in a given temperature and relative humidity, chemically treated wood will have a higher equilibrium moisture content than normal wood.

Fig. 1 shows the equilibrium moisture content of natural wood and wood treated in a saturated solution of sodium chloride. The significance of these curves as applied to chemical seasoning is that during a subsequent kiln drying or air drying in a given relative humidity the surface fibers of salt-treated wood have a higher moisture content than the untreated wood just beneath the chemically treated zone.

Chemical Seasoning Always Dries Wood from Inside Out

For example, by drying wood properly treated in a saturated solution of sodium chloride in air maintained at a

* *Senior Engineer Forest Products Laboratory Forest Service, U. S. Dept. of Agriculture. The laboratory is maintained at Madison, Wis., in cooperation with the University of Wisconsin.*

constant temperature of 70° F. and at a constant relative humidity of 75 per cent, one can prevent the surface of the wood from shrinking and yet ultimately dry the interior untreated portion of the timber to a moisture content of 15 Per cent. By chemical seasoning methods, therefore, it is possible to dry from the inside out and to prevent the surface fibers from becoming sufficiently dry to induce them to shrink. In this way surface checking is avoided because the surface fibers are not stretched as they inevitably are when kiln dried or air dried without chemical treatment.

The chemical is diffused into the wood. If the moisture content of wood is not high enough to provide a continuous film of water into which the chemical can diffuse, the action of diffusion is impeded. The area in which diffusion can take place increases with the moisture content of the wood. Consequently, the amount, rate, and depth of penetration at which a chemical diffuses into wood are directly associated with its moisture content. In species like oak, for example, there is enough moisture present to support diffusion at a fairly rapid rate for a long time. On the other hand, Douglas fir heartwood, when green, has but little more moisture than is necessary to saturate its cell walls. Consequently, Douglas fir fibers do not have to dry very much before they lose their free water, leaving all the remaining moisture confined to the cell walls. While a chemical will diffuse in hygroscopic moisture the rate is very slow. Thus while Douglas fir is soaking in a chemical solution the chemical diffuses into the water in the wood and the water just beneath the treated zone diffuses outward in the opposite direction toward the surface and eventually is lost to the chemical solution. Owing to its original low moisture content, Douglas fir, when steeped in a hot chemical solution having a relatively low vapor pressure, soon dries enough to slow up the rate of diffusion materially. It has been discovered that 12 by 12-inch Douglas fir timbers have almost the same salt distribution when soaked 1½ months as they have when soaked for a much longer period.

Experience has shown that surface checking control can be accomplished by permitting the chemical to diffuse no deeper than from ½ to ⅝ in. This can be accomplished in from four to 10 days depending on the chemical used and the strength of the solution.

The rate at which Douglas fir timbers dry in a saturated solution of sodium chloride is about the same as that for matched timbers that are not in a bath but are subjected to the attained bath temperature and a relative humidity of 75 per cent. In view of the fact that the drying rate increases with increasing temperature, everything else being equal, it follows that when it is desired to obtain a considerable amount of drying while the timbers are in the solution, the bath should be heated.

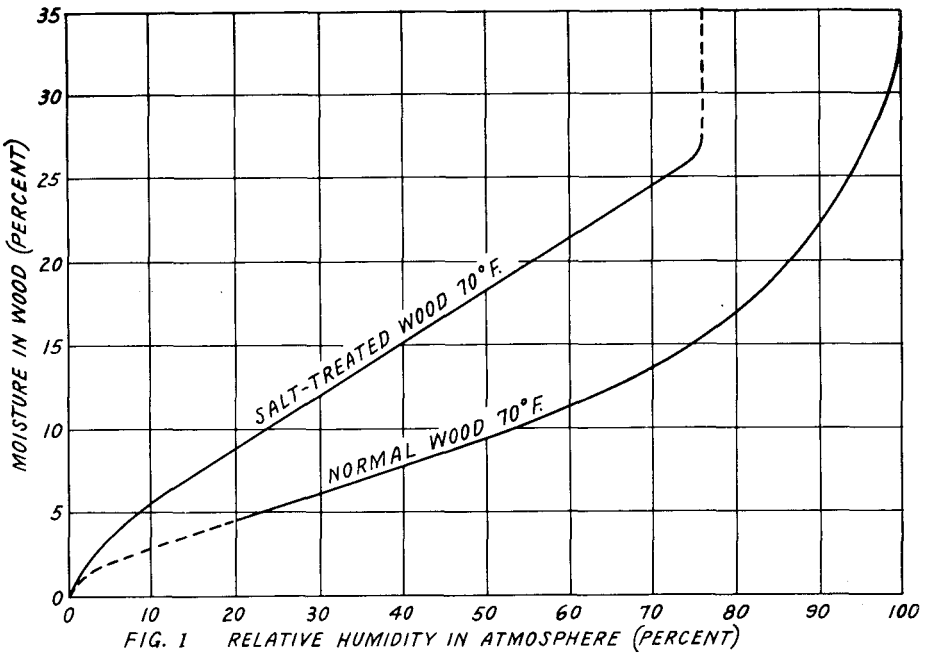

Fig. 1. Equilibrium moisture content of natural wood and wood treated with a saturated solution of sodium chloride. Surface fibres of salt-treated wood have a higher recorded moisture content

Theoretically, the rate at which a chemical will diffuse into wood containing free water is proportional to the absolute temperature of the bath. Since, however, the range in absolute temperature encountered in chemical seasoning is comparatively small, the rate at which a chemical will diffuse into green Douglas fir may be considered a constant. Therefore, with the exception of increasing the drying rate during the soaking process, elevated bath temperatures serve no useful purpose, and due to their deleterious effects on wood should be avoided in treating refractory items. The maximum safe bath temperature which may be used varies with the size and the nature of the item being treated.

Laboratory Technic and Results

The foregoing presents a rough concept of the basic principles involved in the Forest Products Laboratory method of chemical seasoning. The following paragraphs give specific processes with respect to Douglas fir that have resulted satisfactorily.

Flat-sawed Douglas fir planks that are wide and thick require careful kiln drying if surface checking is to be avoided. The expense of this process operates against its general adoption as a commercial practice. Moreover, this class of material will most surely check and split during normal air seasoning. Owing to these seasoning difficulties it is not surprising that wide planks are often shipped green. Chemical seasoning methods are helpful in either kiln drying or air drying such items. After steeping in a saturated solution of sodium chloride maintained at 160" F. for two days, 3 by 12-in. flat-sawed planks of Douglas fir were satisfactorily kiln dried to an average moisture content of 14 per cent in four days by the following schedule:

Temp. °F.	% Rel. Humidity	No. of Days
160	70	2
170	60	1
180	50	1

One lot of flat-sawed 3 by 12-in. Douglas fir planks was boiled in a saturated solution of sodium chloride for four days during which time they dried without degrade to an average moisture content of 12 per cent. At the same time the cores of these planks had an average moisture content of 16.5 per cent.

Another lot of flat-sawed 3 by 12-in. Douglas fir planks was steeped in a 40 per cent solution of invert sugar at 120" F. for two days and kiln dried with the salt-treated planks. (See previous drying schedule.) When removed from the kiln, these planks had an average moisture content of 16 per cent, and were free from any seasoning defect. When treated two days in a saturated solution of sodium chloride 3 by 12-in. planks were air dried in an unheated shed at Madison, Wis., without checking. Matched material when treated with a 40 per cent solution of invert sugar checked under identical drying conditions. The better behavior of the salt-treated planks during air seasoning is, of course, due to the lower vapor pressure of the salt solution.

Side-Cut Timbers

Fig. 2 shows the moisture-time curve of salt-treated 6 by 12-in. timbers and

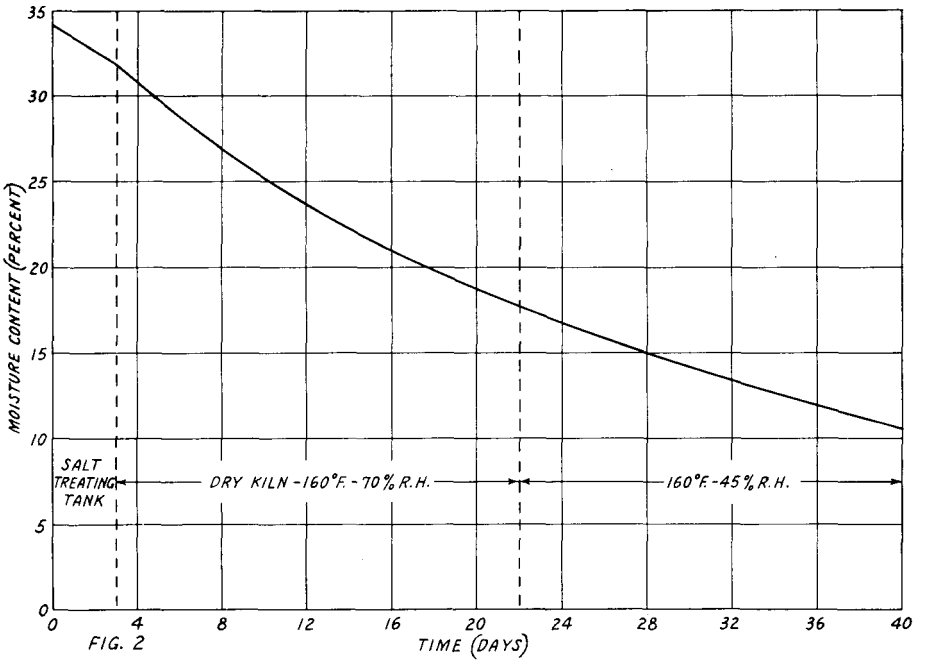

Fig. 2. Moisture-time curve for salt-treated and kiln-dried 6 by 12-in. side-cut Douglas fir timbers

also shows the drying conditions used. In two previous experiments after a two-day and 15-day treatment in a saturated solution of sodium chloride, respectively, each group was kiln dried in a constant temperature of 160° F. and a relative humidity of 60 per cent without the development of seasoning degrade other than some end checking. As all three groups dried at about the same rate, drying with an initial relative humidity of 70 per cent seems the safer and consequently better practice.

Little drying should be permitted until a reasonable amount of chemical has diffused into the timbers if end checking in the bath is to be entirely prevented. The 3-day chemical treatment was planned with this in mind. It consisted of adding sufficient salt to cold water containing the timbers to bring the solution to about 30 per cent of saturation (in equilibrium with about 93 per cent relative humidity) after which it was allowed to stand 24 hours during which time the bath was well agitated. Next the solution was increased to about 70 per cent of saturation in (equilibrium with about 84 per cent relative humidity) and the bath was left for another 24 hours. The solution was then saturated (equilibrium at 75 per cent relative humidity) and the temperature gradually elevated to 160" F. where it was maintained from six to eight hours. If it is necessary to dry timbers of this size perfectly free from end checks, some such treatment as the foregoing must be given. The amount of end checking that occurs when 6 by 12-inch side-cut Douglas fir timbers are treated at room temperatures in a saturated solution of sodium chloride perhaps is not large enough to warrant the additional expense of gradually increasing the solution strength of low vapor pressure solutions. Experiments have shown that when certain end coatings are applied to timbers prior to treatment the hazard of end checking is greatly reduced. Therefore, under certain circumstances perhaps end coatings can be profitably used in chemically seasoning timbers of this kind.

To date, air seasoning experiments following chemical treatment have not included large side-cut timbers. However, the kiln conditions used in drying the foregoing three groups of timbers were more severe than would be normally found in any part of the United States except the arid Southwest. It is reasonable to infer, therefore, that side-cut Douglas fir timbers up to 6 by 12 in. in size can be successfully air seasoned after treating in a chemical solution which has approximately the same vapor pressure as a saturated solution of sodium chloride. It is suggested, however, that for best results the air seasoning should be accomplished in an open shed.

Commercial Aspects

The experiments conducted so far at the Forest Products Laboratory on chemical seasoning have been directed toward only one problem; namely, the drying of large timbers and refractory items of wood without seasoning degrade. The experiments have been so satisfactory as to make it desirable to give serious consideration to the commercial application of the results. For example, thought should be given (a) to the best type of equipment and the ultimate cost of the treatment, (b) to means of preventing the surface of timbers from becoming damp when exposed to high relative humidities, (c) to means of controlling the loss of electric current in items which demand high electrical insulation, (d) to the matter of controlling the corrosion of metal fastenings used in the assembly of salt treated wood.

The experiments indicate that the cost of the absorbed chemical is low. In general, a satisfactory chemical treatment is one in which the weight of the absorbed chemical is equal to two per cent of the weight of the oven-dry wood. In timbers as large as 12 by 12 in. in size this amount of chemical is somewhat excessive, but for purposes of cost estimation the two per cent value may be considered as a constant for all sizes. If the cost of chemical treatment and subsequent kiln drying is assumed to be 30 cents a thousand board feet per day, it is easy to estimate the cost of drying various sized timbers by this process.

Reprinted from Barrel and Box and Packages, December, 1937