

Transient Nonlinear Analysis of Moisture Flow through a Corrugated Fiberboard

Adeeb A. Rahman¹, Thomas J. Urbanik², and Mustafa Mahamid³

¹Assistant Professor, University of Wisconsin-Milwaukee, adeeb@uwm.edu
Department of Civil Engineering and Mechanics. Milwaukee, WI.

²Research Engineer, Forest Product Laboratory, Madison, WI.

³PhD Candidate. UW-Milwaukee. Dept. of Civil Engineering and Mechanics

Abstract

Collapse of fiberboard packaging boxes, in the shipping industry, due to rise in humidity conditions is common and very costly. A 3D FE nonlinear model is developed to predict the moisture flow throughout a corrugated packaging fiberboard sandwich structure. The model predicts how the moisture diffusion will permeate through the layers of a fiberboard (medium and facings). The model predicts the deformation response, the loss of stiffness, and the creep response. The FE results are compared with an experimental set-up used at the Forest Product Laboratory in Madison, WI for a panel subjected to a swept-sine humidity function to study its response to varying humidity function. The panel modeled in this analysis consists of two facings made from liner material separated by a corrugated medium. The liner and medium will be assigned orthotropic stress-strain relations; bilinear stress-strain curves generated from experimental data under variable moisture contents namely 50% and 90% RH. The liner and medium will be modeled as 8-noded shell elements, which allow for curved medium geometry. The major orthogonal directions are the machine direction (MD), the cross machine direction (CD), and the out-of-plane z-direction. The layers are assumed perfectly bonded at juncture lines. The moisture flow is considered in one direction across the thickness of the fiberboard. The fiberboard will be subjected to transient moisture analysis coupled with an edgewise-compressive loading. The transient analysis is dependent on the following material constants: coefficient of moisture diffusivity, and coefficient of moisture expansion. The FE model will provide results showing moisture diffusion flow, creep deformation response in the fiberboard under the action of a static compressive loading and a periodic moisture actual experimental data.

Keywords:

Corrugated fiberboard, finite element analysis FEA, moisture diffusion, liner, medium, coefficient of moisture conductivity, and coefficient of moisture expansion.

The Finite Element Model:

The FE model is developed to represent an actual C-fluted geometry of a corrugated panel. The corrugated fiberboard modeled in this analysis consists of a liner, medium, and interface joints. The liner and the medium are modeled as 8-node shell elements, and the interface joints are modeled by 8-node layered shell elements. Figure 1 is a detailed representation of the FE geometry Rahman 1997. Rahman 2002 reports material properties.

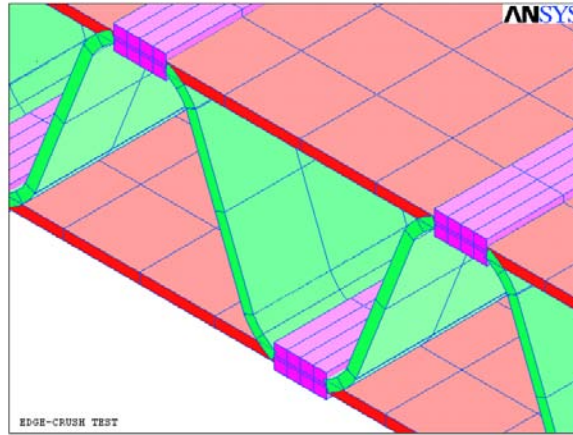


Figure 1: FE geometry of the corrugated fiberboard

A 2 in. by 2 in. corrugated panel is subjected to a steady state moisture flow due to rise in relative humidity from 50% to 90%. The finite element model analyzed is based on the experimental study conducted by Urbanik 1995 27(2). The experiment is conducted on a short column subjected to a single-frequency humidity function as shown in Figure 2.

Theoretical

A derivation of two essential properties namely the coefficient of moisture conductivity D_w and the coefficient of moisture expansion α for the liner and the medium materials are needed to make the finite element analysis possible. Rahman, 2002 shows the derivation of the constants. Table 1 summarizes the values used.

Table 1: Diffusion Properties of Paper Sheet.
Bandyopadhyay, 2001, Rahman, 2002

D_w	$7e-6 \text{ m}^2/\text{s}$
α (Liner)	$5e-5 /\text{C}$
α (Medium)	$2.5e-5 /\text{C}$

Where:

D_w is the coefficient of moisture diffusivity

α is the coefficient of moisture expansion

Moisture Transient Analysis:


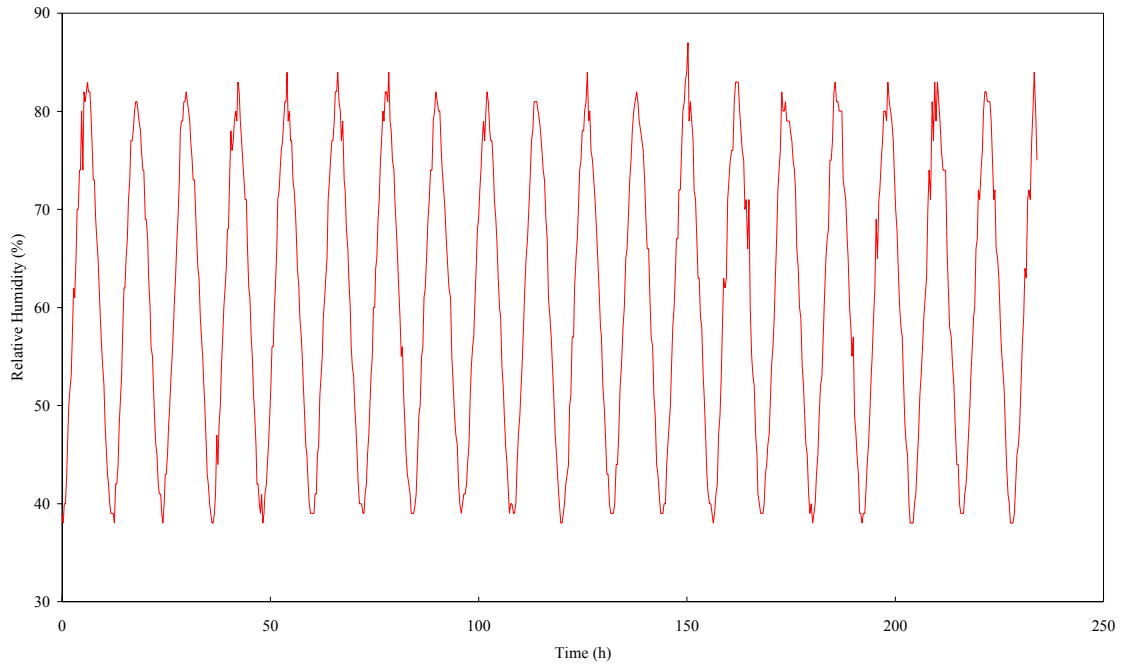


Figure 2: Actual Experimental Relative Humidity Data Vs. Time used as Input (Urbanik 1995 27(2))

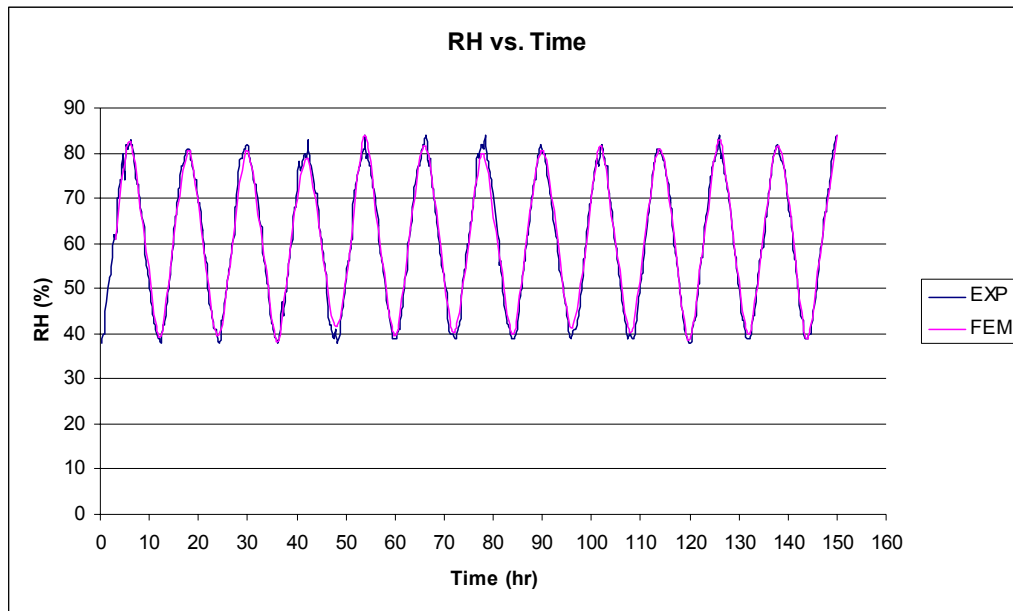

RH variation is between 38% and 86%

Figure 3: RH Experimental Input and Corresponding FEA RH Output form Moisture Diffusion Analysis

Moisture stress analysis

The transient analysis is conducted first in order to calculate the relative humidity values throughout the fiberboard in all the layers as a function of time for time duration of 150 hrs. (6.25 days). The second stage of the analysis is to calculate the fiberboard deformation response (hygroexpansion) due to the change in relative humidity values. This analysis provides the deformation vs. time at different relative humidity values. The maximum deformation occurs at the highest level of RH (86%) and the minimum deformation is recovered at the lower RH value (38%). The deformation response of the structure is shown in Figure 4. The amplitude of deformation is about 0.1 mm. This is close to the amplitude value measured in the experiment. This hygroexpansion response is superimposed on the creep response to predict the overall response of the fiberboard.

Nonlinear creep analysis

This FE research generates the creep model that describes the behavior of a typical paper material. Urbanik 2002 presented a creep model for paper; however, the equations generated do not conform to creep equations' forms available in the finite element program in order to perform the creep analysis. The creep response is dependent on many factors including: material properties, the rate of loading, the time duration, and the relative humidity conditions.

The creep equation for the specimen described followed the following form

$$\varepsilon = \frac{C_1}{C_3 + 1} \sigma^{C_2} e^{-C_4 t^{C_3+1}} \quad (1)$$

Where:

C_1, C_2, C_3, C_4 are constants dependent on the material properties of the paper.

σ is the compressive stress acting on the edge of the specimen, and

t is the time in seconds.

The constants in the creep equations are dependent on the above factors. Changes in the relative humidity are reflected in the values of the constant C_4 . Equation (2) gives the relationship between the constant C_4 as and the RH% within the interval of RH% considered (38%-86%)

Table 2: Constant for Corrugated Short Column Fiberboard's Paper (38% RH)

C_1	5.11e-30
C_2	4
C_3	-0.5882
C_4	-3.85

Table 3: Constant for Corrugated Short Column Fiberboard's Paper (86% RH)

C_1	6.24e-30
C_2	4
C_3	-0.5882
C_4	-3.65

Constant C_4 is affected by the relative humidity. The following equation is derived to relate the value of the constant C_4 to the relative humidity by the following equation:

$$C_4 = \left(\frac{RH - 38}{48} \right) (0.2) - 3.85 \quad (2)$$

The short column finite element model considered is a 2 in. by 2 in. corrugated fiberboard while the experimental fiberboard is 2. in wide and 1.5 in. high (a standard Edge Crush test specimen). Therefore, deflection adjustment for the height is used in order to produce the deflection creep response shown in Figure 4.

Short Column Results:

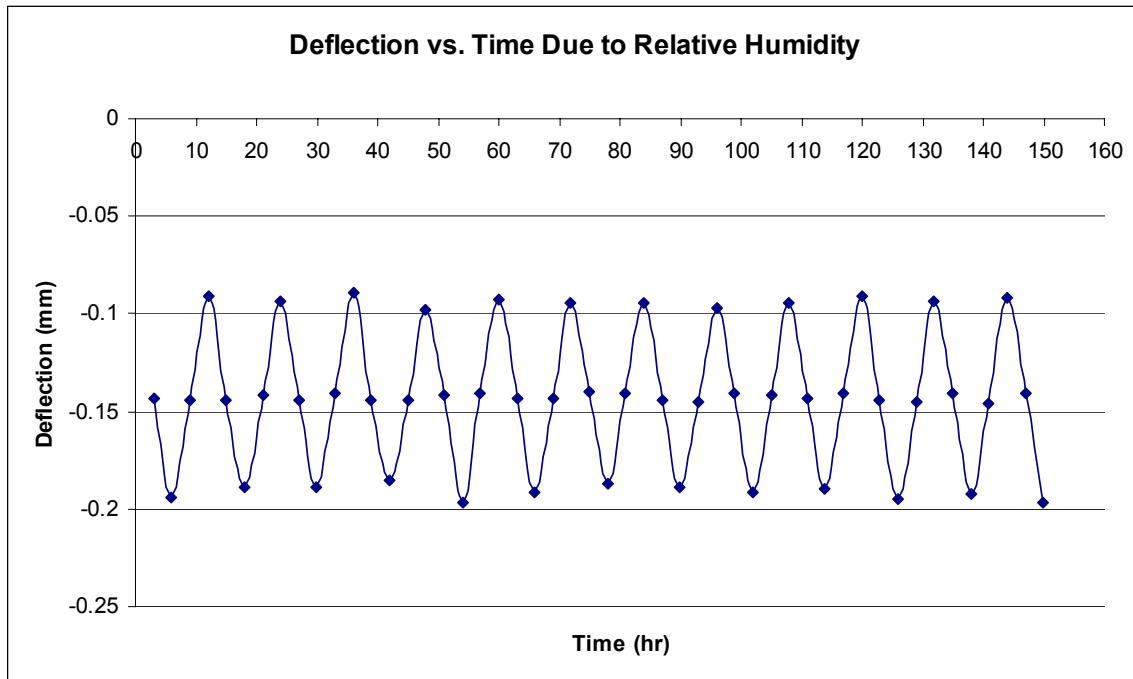


Figure 4: FEA Hygroexpansion Response Due to RH Schedule

Deflection vs. Time Due to Creep and Moisture

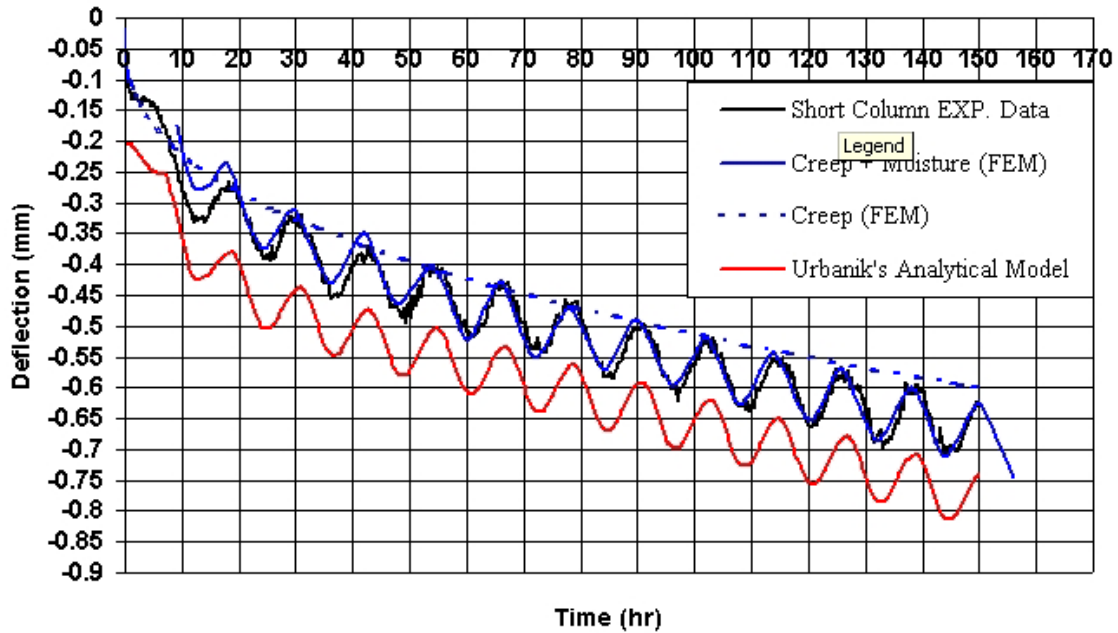


Figure 5: Corrugated Short Column Deflection Due to Creep and Humidity Expansion

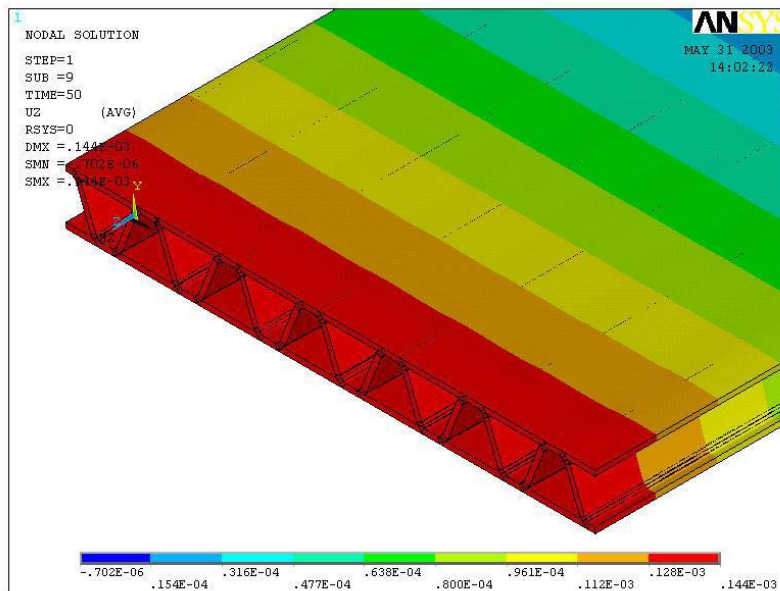


Figure 6: Moisture Deformation due to 86% RH

Discussion and Conclusions

Figure 5 shows the total deformation response from the finite element analysis to the combined effect of humidity expansion and creep deformation. Very close correlation is observed between the FE results and the experimental results. An analytical model derived by Urbanik 1995 27(2) is also shown. The adjustments of the constants in equation (1) allows for calibrating the FFA for different paper type and moisture conditions. The transient moisture analysis, which is a dynamic nonlinear procedure is time consuming, and for a large model can present computational limitation. The nonlinear creep analysis however, is more rapid and can easily be performed for variety constants modification for the creep equation.

The development of FE model to study the moisture expansion and the creep response by establishing a viable creep model for a paper material opens the possibility of considering actual weather data as an input to the model. This can predict the response of a corrugated container box in the field. This FEA is being expanded to predict a box-size-panel and its creep and expansion response to weather data.

Acknowledgements

This research is funded by the USDA-Forest Products Laboratory. Madison, WI.

References

- Bandyopadhyay, A., and Ramarao, B. U., 2001. "Transient Response of Paper Sheet subjected to a Traveling Thermal Pulse: Evolution of Temperature, Moisture and Pressure Fields", *Journal of Imaging Science and Technology*. Vol. 45, No. 6, November/December, pp. 598-608.
- Edmond. P. Saliklis, Thomas J. Urbanik, Bora Tokyay, "A Special Orthotropic Plate Theory Suitable for Use with Ansys". FPL publication 2000.
- Jen Y. Liu, William T. Simpson, "Two-Stage Moisture Diffusion in Wood with Constant Transport Coefficients". *Drying Technology*, 17(1&2), 257-269, 1999.
- Margot Sehlstedt-Persson, Lulea University of Technology, Division of Wood Physics, Sweden, "The Effect of Extractive Content on Moisture Diffusion Properties for Scots Pine and Norway Spruce". COST Action E15 Advances in the drying of wood (1999 – 2003). 3rd Workshop on SOFTWOOD DRYING TO SPECIFIC END-USES. Helsinki, Finland, June 11-13.
- Rahman, Adeb A. "Finite Element Buckling Analysis of Corrugated Fiberboard Panels". ASME Symposium on Cellulosic Materials, AMD-Vol.221, pp. 87-92. 1997, Evanston, IL
- Rahman, A, Urbanik, T. J, and Mahamid, M, 2002. "Moisture Diffusion through a Corrugated Fiberboard under Compressive Loading: Its Deformation and Stiffness Response" PPP 2002, Progress in Paper Physics, Finger lake, NY, pp. 85-88.
- Thomas J. Urbanik and Sung K. Lee, "Swept Sine Humidity Schedule for Testing Cycle Period Effects on Creep". *Wood and fiber Science*, 27(1), 1995, pp. 68-78.
- Urbanik, T. J., 1995. "Hygroexpansion-Creep Model for Corrugated Fiberboard". *Wood and Fiber Science*, Vol. 27(2), 1995, pp. 134-140.

[Home](#)[Papers by Author](#)[Papers by Session](#)

EM03 Electronic Proceedings

The 16th ASCE Engineering Mechanics Conference consisted of 59 technical sessions and 284 presentations. These sessions represented the committees of the Engineering Mechanics Division. The papers span a broad range of topics in traditional and emerging areas in the modeling and simulation of civil and environmental infrastructure systems. All together, the papers demonstrate vigorous research activity that bodes well for the discipline.

This CD contains PDF versions of the papers presented at the conference. Papers may be accessed by author name or by session using the buttons on the left.

UW Organizing Committee

George Turkiyyah (chair)
Pedro Arduino
Laura Lowes
Greg Miller
Dorothy Reed
Harry Yeh

Steering Committee

Denis Bernal
Hamn-Ching Chen
Alex Cheng
Roger Ghanem
Mircea Grigoriu
Dewey Hodges
Wilfred Iwan
Victor Kaliakan
Ahsan Kareem
Ann Kiremidjian
Eric Landis
Loren Lutes
Sami Masri
Jin Ooi
Ronald Pak
Andrew Smyth
Bill Spencer
Henry Stolarski
Gerhart Schueller
Michelle Teng
Franz-Josef Ulm

