

## Effects of Moisture On Aspen-Fiber/Polypropylene Composites

Roger M. Rowell, Sandra E. Lange and Rodney E. Jacobson

USDA, Forest Service, Forest Products Laboratory, Madison, WI, USA

### ABSTRACT

Moisture sorption in fiber-thermoplastic composites leads to dimensional instability and biological attack. To determine the pick up of moisture this type of composite, aspen fiber/polypropylene composites were made using several different levels of aspen fiber (30 to 60% by weight) with and without the addition of a compatibilizer (maleic anhydride grafted polypropylene, MAPP). These composites were tested using short and long term water soaking, boiling water, cyclic liquid water and oven drying, and under various relative humidity conditions. As the level of fiber increased in the composites, the rate and extent of thickness swelling and moisture sorption increased as compared to pure polypropylene. After each cycle of water soaking and oven drying, there was a small but continual increase in moisture content. The presence of MAPP decreased the extent of swelling and moisture pickup.

**Keywords:** aspen fiber, polypropylene, composites, moisture sorption.

### INTRODUCTION

The use of lignocellulosics as fillers and reinforcements in thermoplastics has been gaining acceptance in commodity plastics applications in the past few (Rowell and Sanadi 1998). The lignocellulosics that can be used in thermoplastics can be obtained from many different sources, both from forestry and agricultural resources. The physical form can vary from a fine flour to long agro-based fibers. The cost and performance of the final composite products dictates the type of lignocellulosic to be used in the plastics.

Blending of the plastics with the lignocellulosics may require compatibilization to improve the contact, dispersion, flow and mechanical properties of the composite and has been reported as far back as the late 1960's. Extrusion of lignocellulosics-filled plastics for the automotive industry is well known and has been used for more than twenty years. Typical blending involves the plastic-filler/reinforcement to be shear mixed at temperatures above the softening point of the plastics. The heated mixture is then typically extruded into "small rods", which are then cut into short lengths to produce a conventional pellet. The pellets can then be used in typical injection or compression molding techniques. The direct injection molding process has limitations on the amount of filled/fiber that can be used in the composite and is also likely to be limited to particulate or shorter fiber.

There is still a great deal of basic research going on in many parts of the world in the area of natural fiber/thermoplastic composite materials. This research includes the use of many different types of lignocellulosic-based flours and fibers, different types of thermoplastics,

expanding the amount of flour/fiber in the composites, developing better compatibilization systems, developing testing procedures, and understanding performance through testing and modeling. Equipment development is going forward to produce more efficient mixing systems, faster through put, and new methods of molding/injection.

One of the major research areas of interest in the lignocellulosic/plastics composite area is performance of these materials in outdoor applications (Rowell et al. 1998). Issues of ultraviolet degradation (weathering), moisture up-take, swelling, creep, thermal degradation, and mold and decay resistance are important properties to study to determine the change in performance of these composites as a function of environmental stresses Rowell et al. 2000).

The purpose of this paper is to describe recent results on the moisture sorption of aspen fiber/polypropylene composites.

## EXPERIMENTAL

### *Materials*

Sets of specimens were prepared as follows: aspen fiber was combined with polypropylene (PP) (by weight) alone or with 2% maleic anhydride grafted polypropylene (MAPP) (by weight). The PP homopolymer had a melt flow index of 12 g/10 min. as measured by ASTM D-1238. The MAPP had a number average molecular weight of 20,000, a weight average molecular weight of 40,000 and about 6% by weight of maleic anhydride in the polymer.

Aspen Fiber (%)	Polypropylene (%)	MAPP (%)
30	70	0
30	68	2
40	60	0
40	58	2
50	50	0
50	48	2
60	40	0
60	38	2

The aspen fiber, MAPP and PP (the latter two in pellet form) were compounded in a high intensity thermo-kinetic mixer where the only source of heat is generated through the kinetic energy of rotating blades. The blending was accomplished at 4600 rpm and then automatically discharged at 190 C. The total residence time of the blending operation averaged about 2 min.

The mixed blends were then granulated and dried at 105 C for 4 hours. Test specimen were injection molded at 190 C. using pressures varying from 2.75 MPa to 8.3 MPa depending on the constituents of the blend.

### *Humidity Tests*

Equilibrium Moisture Content. Test specimens were oven dried over night at 105 C and weighed. Specimens were placed in a 90% relative humidity room and left until there was no further weight gain (200 days). The weight gain was determined and used to calculate the

equilibrium moisture content. Three specimens of each type were tested and the results averaged.

**Cyclic Humidity Tests.** Test specimens were oven dried over night at 105 °C and weighed. Specimens were placed in a 30% relative humidity room and left for 25 days. After weighing, the specimens were then placed in a 90% relative humidity room and, again, left there for an additional 25 days. After weighing, the specimens were placed back in the 30% relative humidity room. This process was repeated four times. Three specimens of each type were tested and the results averaged.

### *Liquid Water Tests*

**Rate of Water Sorption.** Test specimens were oven dried over night at 105 °C and weighed. Specimens were placed in water and weights were taken every 15 minutes for the first hour, every hour for the first eight hours, then once a day for 5 days. Each specimen was wiped with a soft towel to remove surface water before weighing. After 5 days, each specimen was re-oven dried for 24 hours at 105 °C and weighed. Three specimens of each type were tested and the results averaged.

**Continuous Soaking.** Test specimens were oven dried over night at 105 °C and weighed. Specimens were placed in water and soaked for seven days and reweighed. The specimens were then returned to water soaking and the process was repeated for 10 weeks. Three specimens of each type were tested and the results averaged.

**Cyclic Water Soaking Tests.** Test specimens were oven dried over night at 105 °C and weighed. Specimens were placed in water, soaked for 7 days, weighed, and re-oven dried. This process was repeated for 10 cycles. Three specimens of each type were tested and the results averaged.

**Boil Test.** Test specimens were oven dried over night at 105 °C and weighed. The specimens were boiled for 2 hours, weighed, and re-oven dried. The process was repeated 10 times for a total of 20 hours of boiling. Three specimens of each type were tested and the results averaged.

## RESULTS AND DISCUSSION

### *Humidity Tests*

Table 1 shows the moisture uptake of aspen-polypropylene composites in a 90% humidity room over time. At 200 days, the specimens were still gaining weight so they had not yet reached equilibrium. As the level of fiber increases in the composites, the amount of moisture increases. In general, the presence of the MAPP decreased the moisture sorption at a given fiber content. This may be due to more intimate contact between fiber and the thermoplastic protecting the fiber from moisture sorption.

**Table 1 - Weight gain in aspen-polypropylene composites at 90% relative humidity after D days**

Aspen/PP/MAPP	Weight Gain					
	25 days	50 days	75 days	100 days	150 days	200 days
0/100/0	0	0	0	0	0.2	0.4
30/70/0	0.7	1.4	1.7	2.1	2.4	2.8
30/68/2	0.7	0.7	1.1	1.5	1.5	2.2
40/60/0	0.7	1.4	1.7	2.0	2.4	3.0
40/58/2	0.4	1.2	1.5	1.9	2.7	3.5
50/50/0	1.3	2.0	2.6	3.6	4.3	5.3
50/48/2	1.5	1.8	2.2	2.9	4.0	5.1
60/40/0	3.7	4.5	5.6	6.0	6.3	6.7
60/38/0	1.6	2.2	3.5	4.4	5.1	6.0

Table 2 shows the change in weight of the composites due to moisture sorption from the cyclic humidity tests. There is an increase in moisture sorption after each cycle and, again, the presence of MAPP in the composites seems to lower the moisture sorption.

**Table 2 - Weight changes in repeated humidity tests on aspen-polypropylene composites cycled between 30 and 90 % relative humidity.**

Aspen/PP/MAPP	Weight Gain							
	30%	90%	30%	90%	30%	90%	30%	90%
0/100/0	0	0	0	0	0	0.2	0	0.4
30/70/0	0.6	0.9	0.7	1.4	0.7	1.4	0.9	1.9
30/68/2	0.4	0.9	0.7	1.2	0.7	1.3	0.9	1.8
40/60/0	0.4	0.9	0.7	1.4	0.7	1.6	0.7	2.1
40/58/2	0.2	1.2	0.8	1.6	1.0	2.0	1.2	3.2
50/50/0	0.5	1.5	1.2	2.5	1.2	2.7	1.2	3.2
50/48/2	0.6	1.3	1.1	2.2	1.3	2.2	1.3	2.6
60/40/0	0.7	2.5	1.5	4.1	1.6	4.1	1.3	4.8
60/38/2	0.2	1.5	1.0	2.6	1.3	2.6	1.3	3.3

### *Liquid Water Tests*

The rate and extent of moisture sorption in liquid water is shown in Figure 1. The rate and extent of moisture sorption increases as the amount of fiber increases. All of the data for all composites is shown in Figure 1 and the figure can be read from top to bottom starting with aspen (60%)-polypropylene (40%) then aspen (60%)-polypropylene (38%)-MAPP (2%) then aspen (50%)-polypropylene (50%) then aspen (50%)-polypropylene (48%)-MAPP (2%). etc., down to 100% PP. This explanation of the multi-plot data is also true for Figures 2 and 7. In all cases, the addition of MAPP decreases the moisture sorption of the composite as a given aspen fiber content.

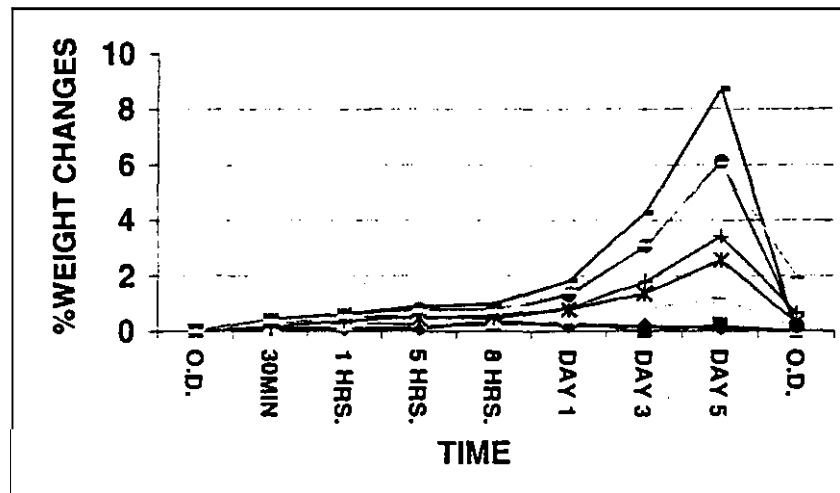


Figure 1 - Rate of moisture sorption of aspen-polypropylene composites in liquid water

Figure 2 shows the data for continuous soaking of the aspen-polypropylene composites in water for 10 weeks. Again, as the amount of fiber increases in the composites, more moisture is sorbed by the composite and the presence of MAPP decreases the amount of moisture sorbed at a given aspen fiber content.

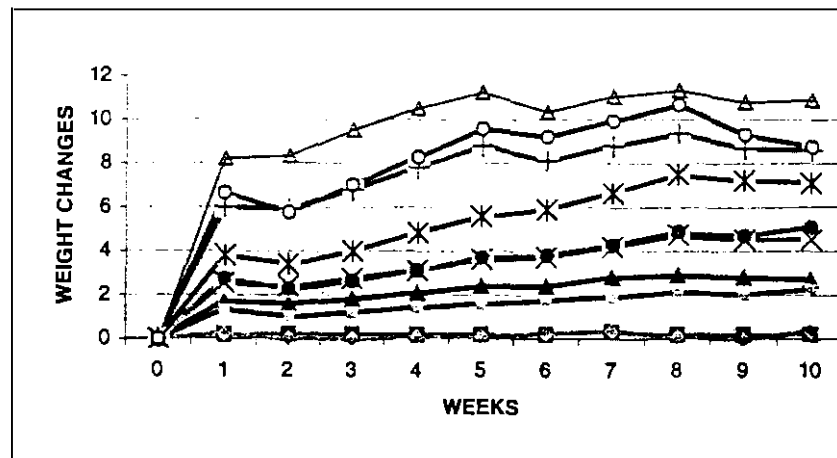


Figure 2 - Extent of moisture sorption of aspen-polypropylene composites in liquid water

Figure 3 shows the results of a cyclic test done on aspen (30%)-polypropylene (70%) composites with and without MAPP starting with an over dry specimen. It can be seen that the presence of MAPP decreases the amount of moisture sorbed in each cycle and the swings in moisture content are decreases.

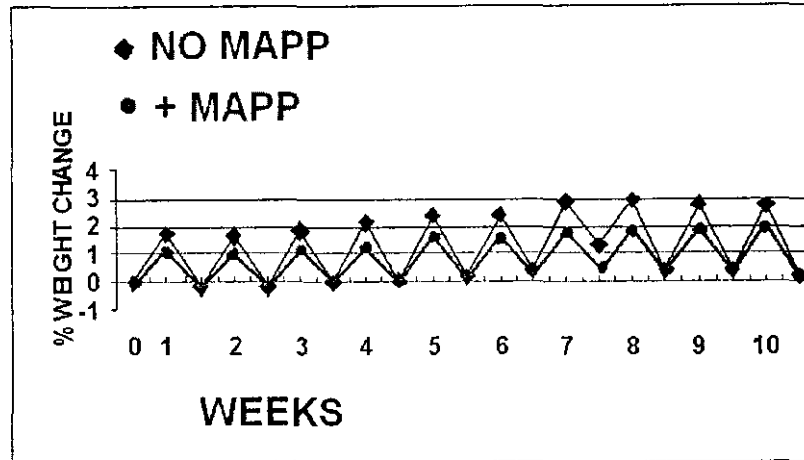


Figure 3 -Cyclic water soaking and oven-drying of ▼ aspen (30%)-polypropylene (70%) and · aspen (30%)-polypropylene (68%)- MAPP (2%) composites.

The same trend is shown in Figures 4 where aspen (60%)-polypropylene (40%) is compared with aspen (60%)-polypropylene (38%)-MAPP (2%) starting with a wet specimen. The presence of MAPP reduces the amount of moisture sorbed.

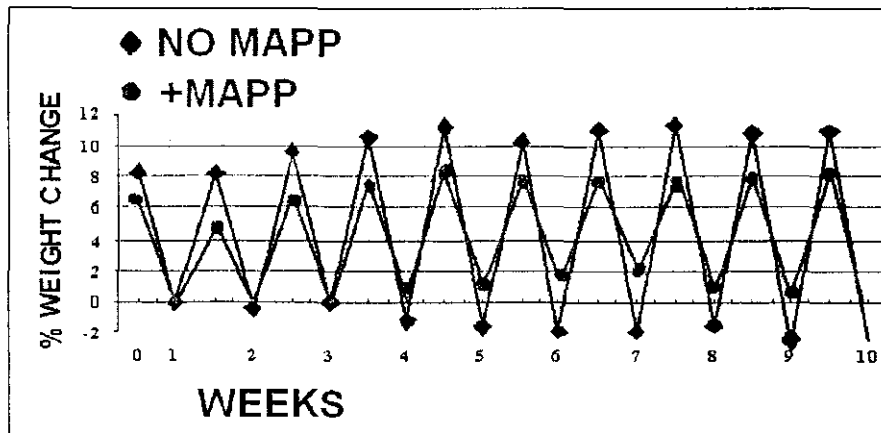


Figure 4 - Cyclic water soaking and oven-drying of ▼ aspen (60%)-polypropylene (30%) and · aspen (60%)-polypropylene (28%)-MAPP (2%) composites.

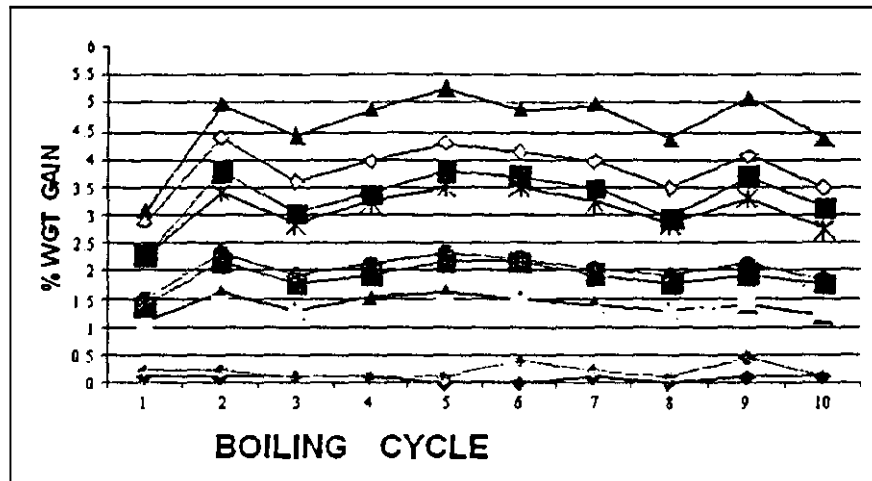


Figure 5 - Moisture sorption of aspen-polypropylene composites after the boiling-oven drying tests.

Figure 5 shows the results of the boiling test. Most of the weight gain that results from boiling takes place in the first boiling cycle and little change occurs in following boiling cycles.

## CONCLUSIONS

Adding agro-based fibers to polypropylene composites provides a strategy to produce composites that are lower in cost, less abrasive on processing equipment than mineral fillers, and improves strength properties as compared to composites containing no fiber. The addition of maleic anhydride grafted polypropylene to these composites improves strength properties even more.

Depending on the amount of fiber, composites exposed to high humidity or submerged in water or boiled for long periods of time resulted in a continual increase in moisture content. The higher the fiber content, the higher moisture sorption. Under cyclic humidity and water soaking conditions, the composites showed a small but steady increase in moisture sorption with each humidity/wetting cycle. Above about 50% fiber content, fiber to fiber contact increases in these composites, resulting in more fiber to fiber wicking so moisture gain goes deeper into the composite and continues with time.

The presence of MAPP decreases moisture sorption in both high humidity and liquid water tests as compared to specimens at the same aspen fiber content. This may be due to the increase in compatibilization resulting from more contact between hydrophilic fiber and hydrophobic plastic.

## REFERENCES

- Rowell, R.M., D.F. Caulfield, G. Chen, W.D. Ellis, R.E. Jacobson, S.E. Lange, R. Schumann, A.R. Sanadi, J.J. Balatinecz, and M. Sain 1998. Recent advances in agro-fiber/thermoplastic composites. In, Proceedings Second international Symposium on Natural Polymers and Composites, L.H.C. Mattoso, E. Frollini, and A. Leao, eds., Atibaia, Brazil, 11-20, May.
- Rowell, R.M., S.E. Lange and R.E. Jacobson. 2000. Weathering performance of plant-fiber thermoplastic composites. *Mol. Cryst. And Liq. Cryst.* 353:85-94.
- Rowell, R.M. and A.R. Sanadi, eds. 1998. Proceedings of the Fourth International Conference on Woodfiber-Plastic Composites, Forest Products Society, Madison, WI, May 12-14, 324 pp.
- Sanadi, A.R., D.F. Caulfield, and R.M. Rowell 1994. Reinforcing polypropylene with natural fibers. *Plastic Engineering*, Vol L(4): 27-28.
- Sanadi, A.R., D.F. Caulfield, R.E. Jacobson, and R.M. Rowell 1995. Renewable agricultural fibers as reinforcing fillers in plastics: Mechanical properties of kenaf fiber-polypropylene composites. *Ind. Eng. Chem. Research*, 34:1889-1896.
- Sanadi, A.R., D.F. Caulfield, and R.E. Jacobson 1997. Agro-fiber/thermoplastic composites. Paper and composites from ago-based resources, R.M. Rowell, R.A. Young and J.K. Rowell, eds., Chapter 12, 377-402, CRC Lewis Publishers, Boca Raton, FL.

# PROCEEDINGS

*7<sup>th</sup> Pacific Rim*

*Bio-Based Composites Symposium*

Nanjing, China  
October 31<sup>th</sup> - November 2<sup>nd</sup>  
2004

## Volume1

Organized By  
College of Wood Science and Technology and the Wood-based Panel Research  
Institute, Nanjing Forestry University, Nanjing, 210037, China

Sponsored By  
National Natural Science Foundation of China  
Research Centre of Fast-growing Trees and Agro-fiber Material Engineering, Jiangsu,  
China

Published By  
Science & Technique Literature Press

Copyright © 2004



Nanjing Forestry University

All Rights Reserved

## Editors

Xiaoyan Zhou

Changtong Mei

Juwan Jin

Xinwu Xu

### **Statement of Procedure**

Nanjing Forestry University is the copyright holder in the compilation entitled the 7th Pacific Rim Bio-Based Composites Symposium. Nanjing Forestry University is authorized to and does grant permission to copy any paper herein with proper attribution upon request. The authors also retain their individual copyrights. Permission to copy is *granted* for nonprofit use.

The views expressed in this publication represent the views of the author as an individual and do not necessarily reflect the views of Nanjing Forestry University.