

# Principles of Minimum Cost Refining for Optimum Linerboard Strength

Thomas J. Urbanik and Jong Myoung Won

## ABSTRACT

The mechanical properties of paper at a single basis weight and a single targeted refining freeness level have traditionally been used to compare papers. Understanding the economics of corrugated fiberboard requires a more global characterization of the variation of mechanical properties and refining energy consumption with freeness. The cost of refining energy to increase paper performance is of the same magnitude as the cost of adding fiber to obtain an equal increase in performance; the costs of energy and fiber vary dramatically with geography and market conditions. We provide formulas that can be programmed into a spreadsheet to graphically examine market condition and performance scenarios. We characterize a recycled linerboard and determine the market conditions that favor increased refining compared to increased fiber.

## KEYWORDS

Cost optimization, Economics, Linerboard strength, Recycling.

## INTRODUCTION

An important step in papermaking is the mechanical refining of pulp fibers (conventionally via disc refiners) to generate optimum mechanical properties of the paper. Researchers have improved the strength properties of paper made from recycled fiber by blending the fiber with virgin fiber and chemical additives (1), using chemical treatment, and modifying the paper machine. Refining is the most practical

process and has been adopted for mill production. However, the more the initial pulp is refined, the more difficult it is to restore the initial strength of recycled pulp through refining (2). Tensile strength has been the property most investigated (2,3). Data are limited on how refining affects paper compressive strength, stiffness properties, or caliper.

The Forest Products Laboratory has researched the feasibility of using small-diameter trees, waste wood, and unconventional wood species for papermaking using an experimental refiner and formed handsheet specimens. The laboratory relationship between refining variables and paper performance provides insight into a process that is undoubtedly more complicated on an industrial scale. Mechanical refining is an energy-intensive process at both the laboratory and industrial scale. As we shall demonstrate, the cost of refining energy to increase paper performance is of the same magnitude as the cost of adding fiber to obtain an equal increase in performance.

In a study of important variables affecting corrugated fiberboard, Koning and Haskell (4) explored the effects and interactions of seven typical papermaking factors (wood species, pulp yield, type of refiner, refining consistency, amount of refining, wet-press pressure, and surface) on various strength properties of 205-g/m<sup>2</sup> linerboard handsheets. Among the properties investigated, compressive strength, modulus of elasticity, and thickness, which are known to relate to the compressive strength of corrugated fiberboard boxes, were consistently and significantly affected by the freeness level achieved by refining. In general, the authors found that the lower of two freeness levels investigated resulted in better linerboards by virtue of increasing overall strength.

Greater linerboard strength can thus be obtained at a lower freeness by more refining, but at a higher energy cost. Greater linerboard strength can also be obtained at a higher basis weight with a proportionally higher fiber cost. When the linerboard is considered as a component in corrugated fiberboard and the compressive strength of a box is important, the most economical linerboard in terms of fiber

---

*Urbanik is Research Engineer: USDA Forest Service, Forest Products Laboratory, Madison, Wisconsin 53726. turbanik@fs.fed.us*

*Won is Professor: Dept. of Paper Science & Engineering, College of Forest Sciences, Kangwon National University, Chunch 200-701, Korea. wjm@mail.kangwon.ac.kr*

and refining energy inputs is one with the minimum total cost of fiber and energy that yields the required box compressive strength. The generalization that lower freeness is better is not as evident.

Linerboard in corrugated fiberboard specified by edgewise crush strength and recycled corrugated medium are produced through the use of higher process refining levels compared to that used for conventional containerboards. Refining energy is among the most costly process variables in containerboard production. The benefits of process refining in combination with the basis weight of the components is important to understanding the economics of corrugated fiberboard.

## OBJECTIVE

We compare the cost and performance of two kinds of linerboard: (a) expensive-to-process but lightweight linerboard made at a low basis weight from highly refined pulp and (b) cheaper-to-process but heavier linerboard made from less refined pulp and more fiber. The empirical variations of refining energy consumption with freeness and variation in mechanical properties with freeness are used to examine theoretically how the performance of the linerboard facing in Corrugated fiberboard relates to the total cost of energy and fiber. Results quantify the optimum refining level that yields fiberboard with adequate performance at the lowest cost of energy plus fiber.

Understanding the effect of refining on paper properties at the laboratory scale is a necessary first step in optimizing industrial production. Production costs emanating from paper machine speed, scheduling efficiency, inventory and distribution, etc., are ultimately important but are not examined in this study. Refining to a low freeness level reduces the drainage rate on the paper machine and might be constrained by a practical cost in actual production. Increasing a paper's basis weight increases its drying time and shipping costs per unit area of paper. The final economics are a function of the effects and interactions among refining, basis weight, and production variables. The results of this study provide a methodology for quantifying the economic feasibility of new materials and for establishing boundaries in a more broadly designed industrial experiment.

## MATERIALS AND TESTS

A single commercial linerboard (94% kraft pulp and 6% recycled corrugated containers) was recycled into pulp and refined at three levels of consistency: 5%, 8%, and 12%. Linerboard material was first pulped in a 50 liter Voith (Heidenheim, Germany) laboratory pulper at 10% consistency for 30 minutes and with nominal hot water.

The pulp slurry was thickened and refrigerated for later use.

Atmospheric refining was later carried out on a 305-mm Sprout-Waldron (Muncy, Pennsylvania) single-disc refiner with C2976 plates. Refining at each level of consistency combined with each of three levels of refiner plate gap (102, 178, and 254 mm) was done at up to three freeness levels. The processed pulps at 5% and 8% consistency were refined with one to three passes through the refiner. The processed pulp at 12% consistency was refined with one or two passes through the refiner. Canadian standard freeness (CSF) measured according to TAPPI Test Method T 227 (5) and cumulative specific energy consumption were determined for the pulp after each pass through the refiner.

Handsheets at three levels of basis weight (BW) (nominally 126, 185, and 205 g/m<sup>2</sup>) were made from each of the 24 refined pulps. For comparison, the freeness of a control material was determined from unrefined pulp, and control handsheets were made from unrefined pulp at the three BW levels. Freeness and specific energy consumption levels determined for the pulps and actual average BW level for the respective handsheets are given in Table 1.

Compression load-strain curves and bending stiffness data that could be used to compute the compressive strength and buckling strength of a facing microplate in corrugated fiberboard were determined from handsheet specimens. Compression load-strain curves up to failure were produced with the apparatus described by Gunderson (6). Bending stiffness in a Taber instrument was determined following TAPPI T 489 (7). The surface-to-surface thickness (caliper) was determined by TAPPI T411 (8).

Prior to testing, materials were preconditioned in a dry environment below 30% RH and then conditioned at 50% relative humidity (RH). All tests were conducted in a conditioned environment at 23°C and 50% RH in accordance with ASTM Standard D 685-93(9).

## RESULTS AND DISCUSSION

### Energy Model

Our data on freeness were found to vary linearly with specific energy consumption and with interactions among consistency, plate refiner gap, and specific energy consumption according to the statistical equation

$$F = \alpha + \beta_0 \text{ SEC} + \beta_1 C \text{ SEC} + \beta_2 C G \text{ SEC} \quad (1)$$

where

$F$  is freeness (mL CSF),

SEC specific energy consumption (W-h/kg),

$C$  consistency (%), and  
 $G$  plate refiner gap ( $\mu\text{m}$ ).

Statistically fitted coefficients obtained via a least squares regression were determined as  $\alpha = 732$ ,  $\beta_0 = -0.179$ ,  $b_1 = -0.0250$ ,  $\beta = 7.37 \times 10^{-5}$ . The standard errors associated with  $\alpha$ ,  $\beta_0$ ,  $\beta_1$ , and  $\beta_2$  are 0.6%, 4.0%, 4.2%, and 5.8%, respectively, as a percent magnitude of the fitted coefficients. Expanding Eq. (1) with additional coefficients applied to  $C$ ,  $G$ ,  $CG$ , and  $G$  SEC was not found to improve the fit to data significantly.

The fit of Eq. (1) to our data (Table 1) is shown in Figure 1 in terms of the inverse expression

$$\text{SEC} = \frac{F - \alpha}{\beta}$$

where

$$\beta = \beta_0 + \beta_1 C + \beta_2 C G \quad (3)$$

Equation (2) with Eq. (3) as input expresses the behavior that for each combination of fixed  $C$  and  $G$ , the respective SEC- $F$  plot passes through a common abscissa  $\alpha$  and has a slope  $1/\beta$  depending on  $C$  and  $G$  (Fig. 1). The fitted level of  $\alpha$  predicts the pulp freeness prior to refining and is within

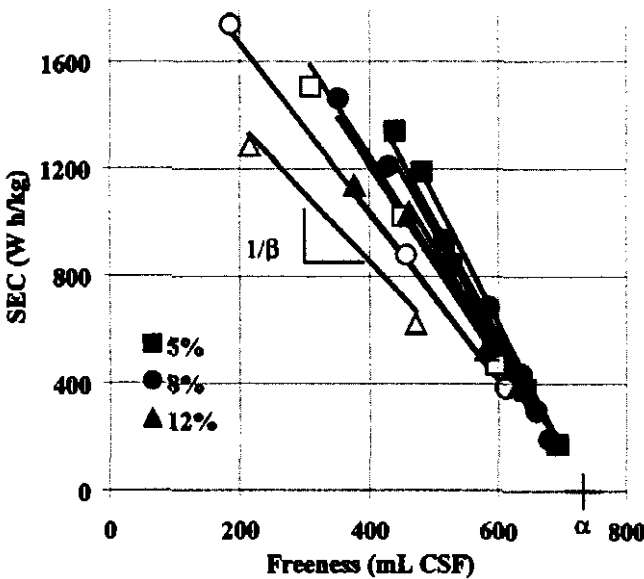


Figure 1. Variation of total specific energy consumption (SEC) with freeness for linerboard pulp refined at nine combinations of consistency at 5%, 8%, or 12% and refining plate gap at 102, 178, or 254  $\mu\text{m}$ . The legend shown is for the three consistency levels and a 254  $\mu\text{m}$  plate gap. Points on the graph are shaded white (102  $\mu\text{m}$ ), gray (178  $\mu\text{m}$ ), or black (254  $\mu\text{m}$ ) to indicate other levels of plate gap. The linear fits to data pass through a common abscissa  $\alpha$  and have slopes  $1/\beta$  that depend on consistency and plate gap according to Eq. (3).  $r^2 = 0.986$ .

4% of the actual determination of 704 mL CSF for the control material (Table 1).

Although Eq. (2) provides a way to accurately interpolate among the data of this study, it does not predict an increasing energy consumption approaching infinity as a zero freeness level is sought. Equation (2) is sufficient for understanding the performance of our experimental refiner within the scope of this study. For commercial refiners and other input variables that affect refining energy consumption, more mechanistic equations' would need to be considered.

### Mechanical Property Model

Data on the variation of compression load  $P$  with compression strain  $\epsilon$  were reduced to average parameter values  $c_1$  and  $c_2$  in a fit of the equation

$$P = c_1 \tanh(c_2/c_1 \epsilon) \quad (4)$$

up to the ultimate strength  $P_u$  at failure. The initial slope of Eq. (4) is given by  $c_2$ . Parameter  $c_1$  is an asymptotic level of  $P$  if Eq. (4) is extrapolated to an infinite  $\epsilon$ . The fitted values of  $c_1$  and  $c_2$  along with the determinations of  $P_u$ , bending stiffness  $D$ , and caliper  $t_c$  are given in Table 1. Strength and stiffness are given in terms of a unit width of specimen.

Variation of each mechanical property  $Q$  with  $BW$  and  $F$  (Table 1) was statistically analyzed with the empirical formula

$$Q = b_0 + b_1 \left( \frac{BW}{BW_0} \right)^{b_2} + b_2 \left( \frac{F}{\alpha} \right)^{b_3} + b_3 \left( \frac{BW}{BW_0} \right)^{b_4} \left( \frac{F}{\alpha} \right)^{b_5} \quad (5)$$

Fitted coefficients for each case of  $Q$  represented by  $c_1$ ,  $c_2$ ,  $P_u$ ,  $D$ , and  $t_c$  are given in Table 2 with normalizing inputs in terms of the lowest nominal basis weight,  $BW_0 = 126$  and  $\alpha = 732$  mL CSF.

Equation (5) is a statistical linear combination of variables  $BW$ ,  $F$ , and interaction  $BW F$  with optimum exponential powers applied. The number of coefficients for each case of  $Q$  in Table 2 is for the most accurate fit of Eq. (5) that is statistically significant based on the statistical  $F$ -test at the

<sup>1</sup> Note that Eq. (2) should not be extrapolated below the freeness levels of this study. For a more mechanistic relation between SEC and  $F$  including lower freeness levels, the equation given by

$$\text{SEC} = \frac{\alpha}{2\beta} \ln \left( \frac{F}{2\alpha - F} \right)$$

is noteworthy. This example of a more general equation approximates Eq. (2) at our experimental levels of  $F$  and also approaches infinity as  $F$  approaches zero.

**Table 1. Mechanical properties of handsheets made at three nominal BW levels from pulps refined at various levels of consistency and refiner plate gap (*G*), measured freeness level (*F*), and total specific energy consumption (SEC) resulting from one to three refiner passes<sup>a</sup>**

5% consistency										8% consistency												
<i>G</i>	<i>F</i>	SEC	BW	<i>c</i> <sub>1</sub>	<i>c</i> <sub>2</sub>	<i>P</i> <sub>u</sub>	<i>D</i>	<i>t</i> <sub>c</sub>		<i>G</i>	<i>F</i>	SEC	BW	<i>c</i> <sub>1</sub>	<i>c</i> <sub>2</sub>	<i>P</i> <sub>u</sub>	<i>D</i>	<i>t</i> <sub>c</sub>				
μm	mL	W·h/kg	g/m <sup>2</sup>	kN/m	kN/m	kN/m	mNm	μm		μm	mL	W·h/kg	g/m <sup>2</sup>	kN/m	kN/m	kN/m	mNm	μm				
254	691	176	129	3.04	811	2.40	6.91	257		254	678	196	121	2.84	766	2.20	6.82	257				
			185	4.46	1,096	3.55	11.49	363								180	4.38	1,116	3.62	11.80	368	
			207	5.12	1,157	4.01	13.79	406									205	5.01	1,232	4.18	14.07	406
528	843	128	3.63	890	2.99	6.70	229		636	436	128	3.32	851	2.71	7.13	249						
			188	5.69	1,311	4.57	11.18	251							187	5.27	1,269	4.47	11.98	347		
			206	6.31	1,394	5.36	12.62	347							208	5.84	1,369	4.76	13.62	373		
481	1,189	127	3.97	948	3.04	6.62	216		428	1,210	127	4.10	984	3.00	6.71	213						
			183	6.13	1,339	4.92	10.61	300							184	5.89	1,337	4.57	10.25	297		
			205	6.33	1,420	5.33	12.47	343							204	6.58	1,474	5.41	13.19	338		
178	642	379	129	3.28	825	2.61	6.92	249		178	659	301	124	3.34	838	2.55	6.66	244				
			187	5.01	1,136	4.04	11.32	353							185	4.81	1,184	4.08	11.96	361		
			208	5.49	1,242	4.59	13.69	399							202	5.31	1,270	4.61	13.47	389		
517	933	126	3.77	896	3.08	6.55	221		585	685	124	3.40	832	2.72	6.70	234						
			189	5.88	1,319	4.81	11.18	307							184	5.23	1,224	4.53	11.29	328		
			202	6.42	1,483	5.45	12.52	340							201	5.97	1,356	5.11	12.99	358		
438	1,341	125	3.90	938	3.03	6.47	206		351	1,463	127	4.27	999	3.07	6.40	201						
			183	6.07	1,350	5.01	10.80	297							184	6.34	1,396	4.91	10.67	287		
			197	6.77	1,491	5.45	11.75	318							201	7.01	1,525	5.77	12.64	323		
102	596	471	128	3.26	809	2.68	6.65	236		102	611	386	125	3.24	838	2.71	6.78	244				
			185	4.97	1,174	4.07	11.02	335							184	5.06	1,219	4.41	11.36	340		
			203	5.51	1,296	4.62	12.69	361							205	5.54	1,303	4.77	13.38	376		
451	1,024	128	3.95	947	3.15	6.59	211		456	879	128	3.39	848	2.56	5.02	206						
			185	6.19	1,383	4.95	10.61	302							196	5.77	1,289	4.81	11.03	307		
			203	7.09	1,525	5.68	12.47	326							220	6.66	1,505	5.49	13.46	348		
309	1,506	127	4.28	991	3.24	6.31	201		185	1,739	125	4.25	1,004	2.99	6.40	198						
			185	6.73	1,511	5.09	10.82	284							186	7.04	1,588	5.17	10.47	287		
			208	7.43	1,574	5.95	12.75	323							202	8.00	1,731	5.89	12.03	310		

12% consistency										Control									
<i>G</i>	<i>F</i>	SEC	BW	<i>c</i> <sub>1</sub>	<i>c</i> <sub>2</sub>	<i>P</i> <sub>u</sub>	<i>D</i>	<i>t</i> <sub>c</sub>		<i>F</i>	BW	<i>c</i> <sub>1</sub>	<i>c</i> <sub>2</sub>	<i>P</i> <sub>u</sub>	<i>D</i>	<i>t</i> <sub>c</sub>			
μm	mL	W·h/kg	g/m <sup>2</sup>	kN/m	kN/m	kN/m	mNm	μm		mL	g/m <sup>2</sup>	kN/m	kN/m	kN/m	mNm	μm			
254	630	390	127	3.48	835	2.69	6.83	246		704	124	2.82	766	2.02	6.59	264			
			185	5.76	1,286	4.54	10.73	325						186	3.99	1,030	3.20	11.47	386
			201	6.01	1,390	4.96	12.41	361						206	4.95	1,202	4.14	12.77	396
461	1,038	129	4.11	932	3.10	6.60	213												
			184	6.26	1,384	5.04	10.50	295											
			203	6.62	1,439	5.20	12.04	325											
178	580	526	125	3.81	908	2.83	6.39	224											
			190	5.97	1,378	4.78	10.96	318											
			203	6.00	1,367	5.04	12.34	340											
377	1,139	126	4.18	993	3.11	6.42	203												
			182	6.22	1,324	5.01	10.27	287											
			203	6.79	1,520	5.60	12.36	315											
102	471	625	126	3.97	939	2.97	6.34	208											
			185	6.12	1,350	4.88	10.45	310											
			203	6.63	1,500	5.56	11.81	335											
215	1,285	125	4.35	1,005	2.99	6.35	193												
			185	6.73	1,461	5.20	10.74	284											
			204	7.35	1,522	5.94	12.57	320											

<sup>a</sup>BW is basis weight; *c*<sub>1</sub> and *c*<sub>2</sub> are parameters; *P*<sub>u</sub> is ultimate strength; *D*, bending stiffness; *t*<sub>c</sub>, surface-to-surface thickness.

**Table 2.** Evaluations of coefficients obtained from least squares regression fit of Eq. (5) to mechanical property data in Table 1 using  $BW_0 = 126$  and  $\alpha = 732$  mL CSF.


Eq. (5)	Mechanical property				
	$c_1$	$c_2$	$P_u$	$D$	$t_c$
coefficient	(kN/m)	(kN/m)	(kN/m)	(mN·m)	( $\mu$ m)
$b_0$	-0.50	63.0	-1.20	2.72	21.9
$b_1$	5.14	991	4.34	3.66	181
$b_2$	0	0	0.95	0	0
$b_3$	-1.84	-301	-1.86	0.92	78.1
$b_g$	1	1	1	2	1
$b_f$	2	2	4	7	5
$r^2$	0.966	0.961	0.973	0.985	0.972

95% confidence level. Mechanical properties  $c_1$ ,  $c_2$ , and  $t_c$  were found to depend on  $b_0$ ,  $b_1$ ,  $b_3$ , and  $b_1$ ;  $P_u$  depends on  $b_0$ ,  $b_1$ ,  $b_2$ ,  $b_3$ , and  $b_1$ ; and  $D$  depends on  $b_0$ ,  $b_1$ ,  $b_3$ ,  $b_g$ , and  $b_1$ .


Data on each mechanical property acquired at the actual BW level and respective predictions at the nominal BW levels are shown in Figures 2 to 6. For each fit of  $Q$ , it was further verified that expanding Eq. (5) to include coefficients related to  $C$  and  $G$  did not result in a significant improvement.

### Cost Determination


For purposes of this study, we consider the recycled linerboard cost as the sum of the costs attributable

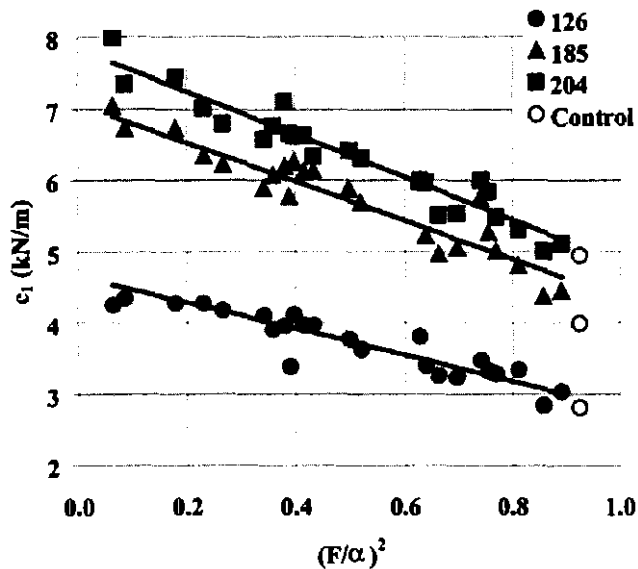

**Figure 2.** Variation of compressive load-strain constant  $c_1$  with freeness ratio  $F/\alpha$  among data in Table 1. Points represent respective mechanical property determined from handsheet at actual basis weight (BW). Lines are predicted property via Eq. (5) based on nominal BW. Legend refers to nominal BW ( $g/m^2$ ) and control material (Table 1).

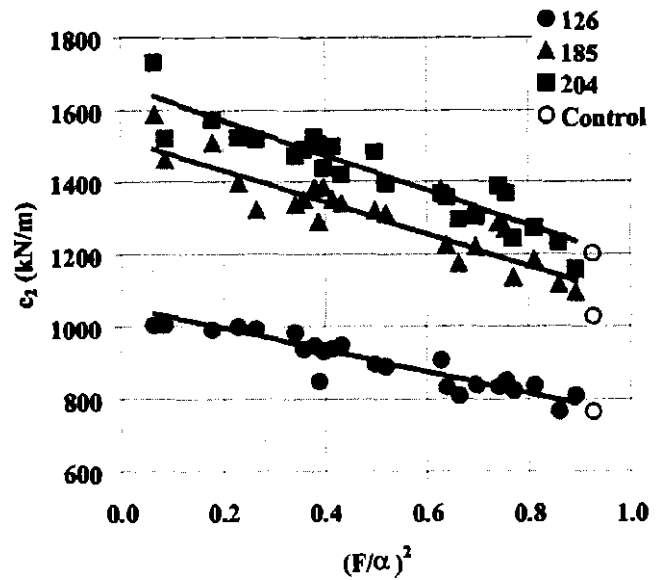

**Figure 3.** Variation of compressive load-strain constant  $c_2$  with freeness ratio  $F/\alpha$  among data in Table 1. See Figure 2 for explanation of points and legend.

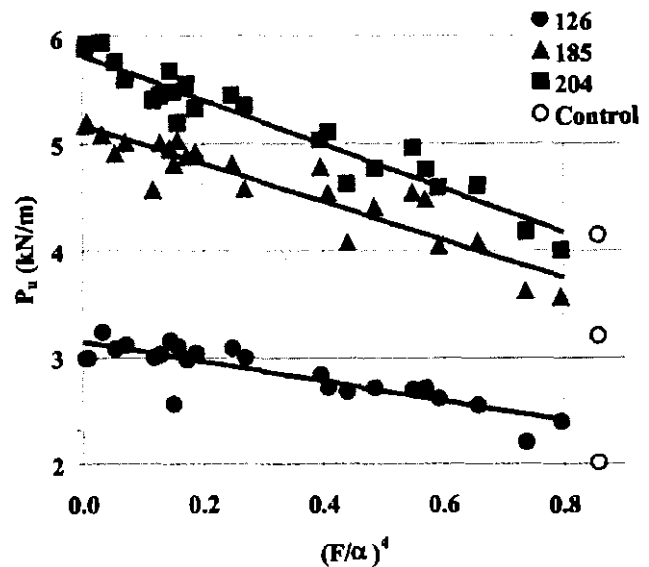

**Figure 4.** Variation of ultimate compressive strength  $P_u$  with freeness ratio  $F/\alpha$  See Figure 2 for explanation of points and legend.

exclusively to fiber and the specific energy consumption of refining. The best example of a relevant commercial raw material representing the fiber would probably be the recycled pulp that enters the head box on the paper machine. The ultimate purchase price of linerboard by the corrugating converter will include other costs of marketing and production beyond the scope of this investigation.

Costs of recycled fiber and energy vary dramatically with geography and market conditions. For instance, one measure of unprocessed fiber cost would be the price of old

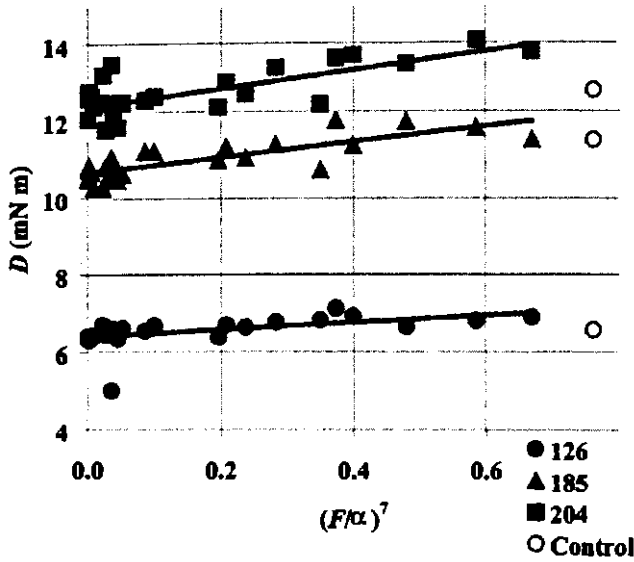


Figure 5. Variation of bending stiffness  $D$  with freeness ratio  $F/\alpha$ . See Figure 2 for explanation of points and legend.

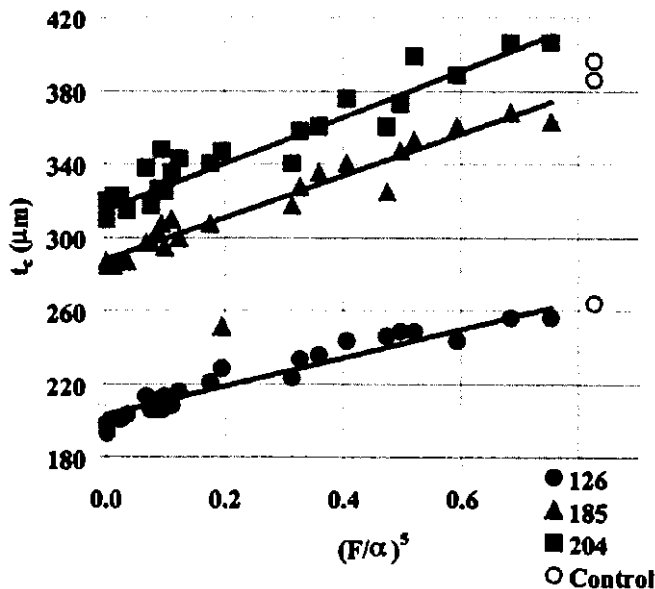


Figure 6. Variation of surface-to-surface thickness  $t_c$  with freeness ratio  $F/\alpha$ . See Figure 2 for explanation of points and legend.

corrugated containers. Prices reported in the North American Factbook (10) varied throughout the year 2000 from \$42.25 per metric ton (t) in New York to \$161.67/t in the San Francisco/Los Angeles area. Electrical energy rates during the winter of 2001 were reported by the Edison Electric Institute (11) to range from 4.4 cents/kW-h for a 1000-kW demand in Missouri to 13.7 cents/kW-h for a 500-kW demand in New York.

In adding these costs, it is helpful to express them in terms of a unit area of linerboard:

$$C_i \left( \frac{\$}{10^3 \text{ m}^2} \right) = C_f \left( \frac{\$}{10^3 \text{ m}^2} \right) + C_e \left( \frac{\$}{10^3 \text{ m}^2} \right) \quad (6)$$

$C_f$  is the cost of fiber in linerboard at a specific basis weight and is computed from the conventional price  $C_F$  reported per ton.

$$C_f \left( \frac{\$}{10^3 \text{ m}^2} \right) = C_F \left( \frac{\$}{\text{t}} \right) \text{BW} \left( \frac{\text{g}}{\text{m}^2} \right) \left( \frac{\text{t}}{1000 \text{ kg}} \right) \left( \frac{\text{kg}}{10^3 \text{ g}} \right) = 10^{-3} C_F \text{BW} \quad (7)$$

$C_e$  is the cost of refining energy in linerboard at a specific basis weight and is computed from the conventional energy rate  $C_E$ .

$$C_e \left( \frac{\$}{10^3 \text{ m}^2} \right) = C_E \left( \frac{\text{cents}}{\text{kW} \cdot \text{h}} \right) \left( \frac{\$}{100 \text{ cents}} \right) \text{SEC} \left( \frac{\text{Wh}}{\text{kg}} \right) \text{BW} \left( \frac{\text{g}}{\text{m}^2} \right) \left( \frac{\text{kWh}}{10^3 \text{ Wh}} \right) \left( \frac{\text{kg}}{10^3 \text{ g}} \right) = 10^{-2} C_E \text{SEC BW} \quad (8)$$

$C_i$  is the combined cost to consider. For example, with fiber at \$100/t and energy at \$0.09/kW-h, the cost components of a 200-g/m<sup>2</sup> linerboard made from pulp refined at 1,000 W-h/kg would be  $\%20/10^3 \text{ m}^2 + \$18/10^3 \text{ m}^2 = \$38/10^3 \text{ m}^2$ .

### Performance Criteria

The compressive strength of a corrugated box is related to the edgewise crush strength of the combined board, which in turn depends on the localized compressive strength of the linerboard facings. If a facing component in corrugated fiberboard is adequately supported against failure by local buckling, its load-carrying capacity approaches  $P_u$  of the linerboard material.  $P_u$  provides an upper bound on strength. A lower bound is the buckling strength  $B_u$  of a facing microplate under simple support conditions and can be determined from the theory by Johnson and Urbanik (12).

For conciseness, we provide equations sufficient for producing the plots in Figures 7 to 9. The complete derivations are provided by Johnson and Urbanik (12, 13). We also limit our analysis to our isotropic handsheet data at standard test conditions as inputs, although the Johnson and Urbanik (12) theory is appropriate to anisotropic properties at arbitrary relative humidity if such data are available.

Buckling strength is given by

$$B_u = c_1 \tanh \hat{\epsilon} \quad (9)$$

where  $\hat{\epsilon}$  is a dimensionless buckling strain computed iteratively from

$$\hat{\epsilon} = \frac{\pi^2 S}{6(1-\nu^2)} \left( 1 + \sqrt{1 - (1-\nu^2) \left( 1 - \frac{2\hat{\epsilon}}{\sinh(2\hat{\epsilon})} \right)} \right) \quad (10)$$

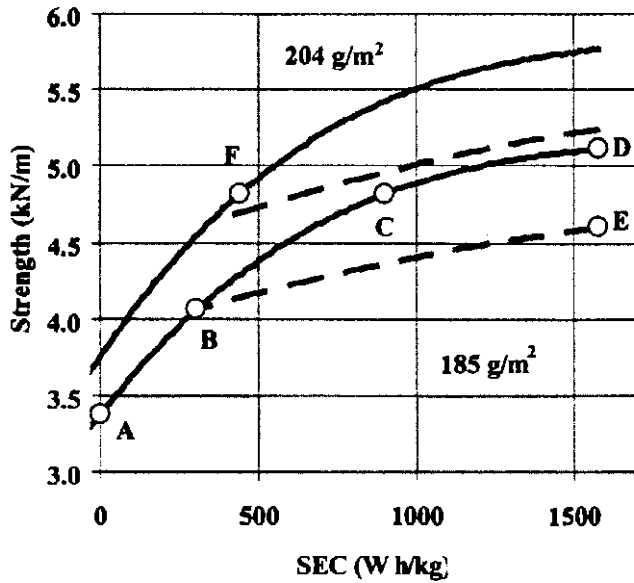


Figure 7. Variation of microplate strength with SEC of refining and dependence on flute size for linerboard at two BW levels. Lower plot (points A–E), 185-g/m<sup>2</sup> linerboard; upper plot (point F), 204-g/m<sup>2</sup> linerboard. Solid lines, predicted  $P_u$  in B- or C-flute corrugated structure; dashed lines, predicted  $B_u$  in A-flute structure.

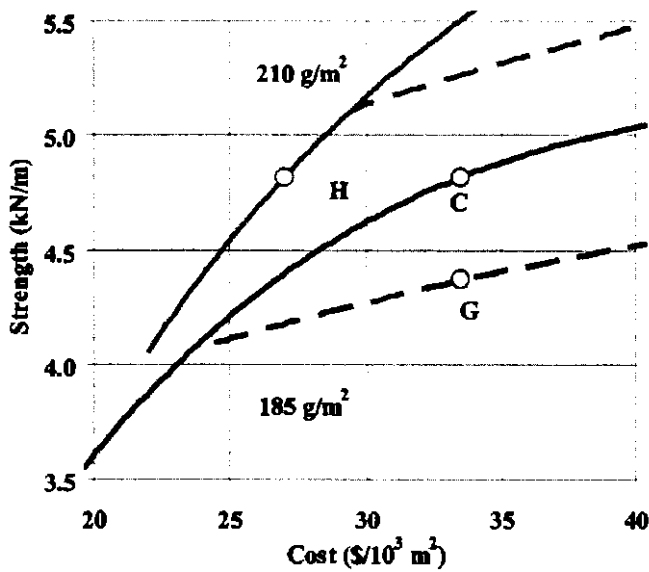


Figure 8. Variation of microplate strength with combined cost components of fiber at  $C_F = \$100/t$  and energy at  $C_E = 9$  cents/kW·h and dependence on flute size for linerboard at two BW levels. Lower plots (points C, G), 185-g/m<sup>2</sup> linerboard; upper plot (point H), 210-g/m<sup>2</sup> linerboard. See Figure 7 for explanation of the line patterns.

An initial estimate of  $\hat{\epsilon}$  is given by

$$\hat{\epsilon} = \frac{\pi^2 S}{3(1 - \nu^2)} \quad (11)$$

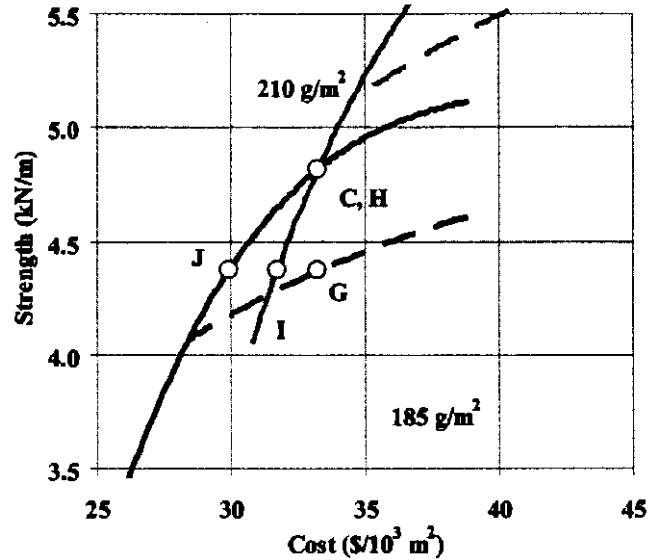


Figure 9. Variation of microplate strength with combined cost components of fiber at  $C_F = \$140/t$  and energy at  $C_E = 5$  cents/kW·h and dependence on flute size for linerboard at two BW levels. Lower plot (points C, J, G), 185-g/m<sup>2</sup> linerboard; upper plot (points H, I), 210-g/m<sup>2</sup> linerboard. See Figure 7 for explanation of line patterns.

Dimensionless microplate stiffness ( $S$ ) in terms of mechanical properties of the paper is inputted from

$$S = \frac{c_2 \left(\frac{t}{l}\right)^2 \sqrt{\frac{\nu_1}{\nu_2}}}{c_1 l^2} = \frac{12D}{c_1 l^2} \quad (12)$$

For simplicity, the second form of  $S$  in Eq. (12) is appropriate to handsheet data only.

Input Sand iteration of  $\hat{a}$  involves the material Poisson's ratios  $\nu_1$ ,  $\nu_2$ , their geometric mean  $\nu$ , thickness  $t$  appropriate to homogeneous material, and microplate width  $l$ . When  $\nu$  is unknown, the average  $\nu = 0.268$  considered in the calculations of Johnson and Urbanik (13) is useful to apply. Using the corrugated flute pitch<sup>1</sup> as input  $l$ , the upper bound on strength at  $P_u$  is apt to apply to corrugated fiberboard having a narrow flute pitch, as in B-flute, or high stiffness facing relative to the linerboard thickness. The lower bound on strength at  $B_u$  is apt to apply to a wider flute pitch, as in A-flute, or low stiffness facing.

The linerboard performance of interest is the strength of a facing microplate in a corrugated fiberboard structure. The strength depends further on the support conditions provided by the corrugated medium but lies somewhere between  $P_u$  and  $B_u$ .  $P_u$  is to be calculated directly from Eq. (5) using

<sup>1</sup> Typical values given by Urbanik (14) are 6.35, 7.21, and 8.47 mm for B-, C-, and A-flute, respectively.

the parameters of mechanical property  $P_u$  from Table 2 as inputs.  $B_u$  is to be calculated from Eq. (9) as an iterative function of Eqs. (10–12) using the parameters of mechanical properties  $c_1$  and  $D$  from Table 2 as inputs and values of  $\nu$  and  $l$ .

### Relation of Performance to Energy Consumption

As Figure 1 shows, the specific energy consumption of refining varied with the refining freeness level for our specific linerboard pulp. As Figures 2 to 6 show, mechanical properties varied with basis weight and freeness for handsheets made from the refined pulp. If the facing components of corrugated fiberboard have properties represented by handsheets, performance would be expected to vary with consumed energy, as shown in Figure 7.

The predicted performance of linerboard facings at two BW levels is plotted in Figure 7. In addition, two ranges of flute size are analyzed. The conditions  $C = 8\%$  and  $G = 178 \mu\text{m}$  are fixed. If a linerboard facing is made to  $185 \text{ g/m}^2$  BW, its maximum strength from pulp refined at various levels would follow the path shown by points A, B, C, and D (Fig. 7) corresponding to calculated freeness levels of 732, 648, 485, and 300 mL CSF, respectively. Increasing levels of refining reduce pulp freeness, increase energy consumption (Fig. 1), and increase strength (Fig. 4). Path A–B–C–D (Fig. 7) quantifies maximum strength in terms of  $P_u$  for a  $185\text{-g/m}^2$  linerboard.

Path A–B–C–D (Fig. 7) is the predicted linerboard performance in a B-flute or C-flute corrugated fiberboard. If the same linerboard is fabricated into an A-flute structure, strength is predicted to follow the path A–B–E (Fig. 7). Path B–E results from a condition where  $B_u$  (Eq. (9)) is less than  $P_u$ . The actual intersection at point B depends on the value of  $l = 8.47 \text{ mm}$  assumed to apply.

A curve predicting the performance of a  $204\text{-g/m}^2$  linerboard is also shown in Figure 7. Point F for a  $204\text{-g/m}^2$  linerboard with a calculated freeness level of 611 mL CSF is at the same strength level as point C for a  $185\text{-g/m}^2$  linerboard. In each case,  $P_u = 4.82 \text{ kN/m}$ . However, point F results from pulp refined to a freeness level consuming 440 W·h/kg, whereas point C results from pulp refined to a freeness level consuming 900 W·h/kg. Strength at point F, which represents more fiber and less consumed energy, is the same strength as that at point C, which represents less fiber and more consumed energy. The better choice for corrugated fiberboard depends on the relative costs of fiber and energy.

### Optimization

The quantification of point C as presented in Figure 7 is shown again in Figure 8 in terms of the cost  $C_t$ , assuming a fiber cost  $C_f$  of \$100/t and an energy cost  $C_e$  of 9 cents/

kW·h. Point C shows that the  $185\text{-g/m}^2$  linerboard would have a strength  $P_u$  of 4.82 kN/m at a cost  $C_t$  of \$33.49/ $10^3 \text{ m}^2$  if used in a B- or C-flute corrugated fiberboard. If the same linerboard is used in an A-flute corrugated fiberboard, the expected strength is reduced 9.5% to a  $B_u$  of 4.37 kN/m (point G, Fig. 8).

The analysis of a  $210\text{-g/m}^2$  linerboard is also plotted in Figure 8. Point H is at the same strength level as point C but at a lower cost  $C_t$  of \$26.99/ $10^3 \text{ m}^2$ . For a required strength of 4.82 kN/m and for our included assumptions, the  $210\text{-g/m}^2$  linerboard is 19% less expensive than the  $185\text{-g/m}^2$  linerboard. The pulp represented by point H is refined to a level of 663 mL CSF compared to 485 mL CSF for the pulp at point C. In this example, it is less expensive to add fiber than to increase refining.

The  $210\text{-g/m}^2$  linerboard (Fig. 8) has another inherent advantage. The Performance predicted by point H is the same for B-, C-, and A-flute structures. By contrast, the  $185\text{-g/m}^2$  linerboard becomes weaker in the A-flute structure, which could generate additional costs. Additional analysis at our assumed conditions would show that the  $210\text{-g/m}^2$  linerboard is more economical than the  $185\text{-g/m}^2$  linerboard at any required strength level.

The analytical results could change if market conditions change. Figure 9 predicts the performance at the same two BW levels assuming a higher fiber cost  $C_f$  of \$140/t and a lower energy cost  $C_e$  of 4.41 cents/kW·h. For these market conditions and for a required strength of 4.82 kN/m, linerboards at both BW levels cost \$33.25/ $10^3 \text{ m}^2$ . Points C and H merge in Figure 9. However, if a lower strength, such as 4.37 kN/m, were required in a B- or C-flute structure, it would cost \$29.92/ $10^3 \text{ m}^2$  (point J, Fig. 9) to use  $185\text{-g/m}^2$  linerboard compared with \$31.72/ $10^3 \text{ m}^2$  (point I, Fig. 9) to use  $210\text{-g/m}^2$  linerboard.

The pulp represented by point J (Fig. 9) was refined to a level of 597 mL CSF compared to 706 mL CSF for the pulp at point I. In this example, when energy costs are low, it is less expensive to expend energy and increase refining than to add fiber. In contrast with the scenario in Figure 8, the  $185\text{-g/m}^2$  linerboard is 5.7% less expensive than the  $210\text{-g/m}^2$  linerboard. This cost advantage is limited to the flute size considered. If the linerboard is required to retain the same strength level in an A-flute structure, it must be refined to 485 mL CSF at a combined cost of \$33.25/ $10^3 \text{ m}^2$  (point G, Figure 9).

### CONCLUSIONS

The mechanical properties of paper at a single basis weight and a single targeted refining freeness level have traditionally been used to evaluate the feasibility of using

small-diameter trees, waste wood, and unconventional wood species for papermaking. While the conclusions drawn may have been valid, we see that a more global characterization of the variation of mechanical properties and refining energy consumption with freeness provides a more rational economic justification of refining levels. At recent price levels, the cost of refining energy to increase paper performance is of the same magnitude as the cost of adding fiber to obtain an equal increase in performance. The costs of energy and fiber vary dramatically with geography and market conditions. We provide scenarios for optimizing the performance of the linerboard component in corrugated fiberboard based on real world data, showing how the lowest cost linerboard depends on market conditions. For the single recycled pulp investigated, an economic justification for increased refining occurs only with a combination of relatively inexpensive energy and expensive fiber. Otherwise, it is more economical to use low refined pulp and heavier basis weight papers.

#### LITERATURE CITED

1. Zhang, M., M. A. Hubbe, R. A. Venditti, and J. A. Heitmann. 2002. Can recycled kraft fibers benefit from chemical addition before they are first dried? *Appita J.* 55(3):135.
2. McKee, R.C. 1971. Effect of repulping on sheet properties and fiber characteristics. *Paper Trade J.* 155(21):34.
3. Lumiainen, J. 1992. Do recycled fibers need refining? *Pap. Puu* 74(4):319.
4. Koning, J.W. Jr. and J.H. Haskell. 1979. Papermaking factors that influence the strength of linerboard weight handsheets. Res. Pap. FPL-323. U.S. Dept. Agriculture. Forest Service, Forest Products Laboratory, Madison. WI.
5. TAPPI. 2004. Official test method T 227, Freeness of pulp (Canadian standard method). TAPPI, Atlanta, GA.
6. Gunderson, D. 1983. Edgewise compression of paperboard: a new concept of lateral support. *Appita* 37(2):137-141.
7. TAPPI. 2004. Official test method T 489, Bending resistance (stiffness) of paper and paperboard (Taber-type tester in basic configuration). TAPPI. Atlanta, GA.
8. TAPPI. 2005. Official test method T 411, Thickness (caliper) of paper, paperboard, and combined board. TAPPI. Atlanta. GA.
9. ASTM. 2002. Standard D 685-93, Standard practice for conditioning paper and paper products for testing. American Society for Testing and Materials, West Conshohocken, PA.
10. Pulp & Paper. 2001. North American Factbook. Paperloop Publications. North Hollywood. CA, p. 171.
11. Edison Electric Institute. 2001. Typical bills and average rates report. Winter 2001, Washington, DC.
12. Johnson, M. W. Jr. and T. J. Urbanik. 1987. Buckling of axially loaded, long rectangular plates. *Wood Fiber Sci.* 19(2):135-146.
13. Johnson, M. W., Jr. and T. J. Urbanik. 1984. A nonlinear theory for elastic plates with application to characterizing paper properties. *J. Appl. Mech.* 51(3): 146-152.
14. Urbanik, T.J. 2001. Effect of corrugated flute shape on fibreboard edgewise crush strength and bending stiffness. *JPPS* 27(10):330-335. ■

Manuscript received for review March 3, 2006.

Revised manuscript received and accepted August 24, 2006.